

Evidence of CO₂ Chemisorption at High Temperature in Lithium Gallate (Li₅GaO₄)

Tatiana Ávalos-Rendón and Heriberto Pfeiffer*

Instituto de Investigaciones en Materiales, Universidad Nacional Autónoma de México, Circuito Exterior s/n Cd. Universitaria, Del. Coyoacán, CP 04510, México DF, Mexico

(Received February 3, 2011; CL-110097; E-mail: pfeiffer@iim.unam.mx)

Li₅GaO₄ was tested as a possible CO₂ captor. Li₅GaO₄ was synthesized by solid-state reaction, structurally characterized, and then thermally treated under a CO₂ flow, from 30 to 900 °C, having the highest CO₂ chemisorption at around 709 °C. The results clearly showed that Li₅GaO₄ is able to trap CO₂ chemically in two different steps. The CO₂ quantity trapped was equal to 8.9 mmol g⁻¹, which is considerably high in comparison to other ceramics.

The increase of carbon dioxide (CO₂) in the atmosphere is claimed to be one of the major contributors to the greenhouse effect and will result in serious global warming issues, such as melting icebergs in the polar regions, hotter summer and winters never seen before, all of them due to the global increment of temperature.¹⁻³

In that sense, in the last years, different lithium ceramics have been proposed as possible CO₂ captors.⁴⁻¹⁰ Among all these ceramics, Li₄SiO₄, Li₄TiO₄, Li₆Zr₂O₇, and Li₅AlO₄, seem to have the best theoretical and experimental CO₂ capture efficiencies.^{7,8,10-15} In fact, in a recent paper Ávalos-Rendón et al.¹¹ proposed Li₅AlO₄ as a new CO₂ captor, and the results presented in that paper showed the highest experimental CO₂ absorption reported in the literature, up to now, for this kind of materials, 16.4 mmol g⁻¹ (maximum CO₂ theoretical capacity, 19.8 mmol g⁻¹).

On the other hand, lithium gallate (Li₅GaO₄) has been scarcely studied, and it has been mainly tested as a lithium ion conductor.^{16,17} Additionally, it has to be pointed out that Li₅GaO₄ and Li₅AlO₄ are isostructural materials. It is important, as Li₅AlO₄ has been shown to be one of the best possible CO₂ captor ceramics.¹¹ Both ceramics have orthorhombic phases, where the cell parameters varied from 9.173, 9.094, and 9.202 Å to 9.087, 8.947, and 9.210 Å for Li₅GaO₄ and Li₅AlO₄, respectively.^{18,19} Therefore, based on the high lithium content of Li₅GaO₄ and the fact that it is an isostructural material with Li₅AlO₄, the aim of this work was to study and demonstrate if Li₅GaO₄ is able to capture CO₂, through a similar mechanism to that reported previously for other lithium ceramics.

Li₅GaO₄ was synthesized by solid-state reaction using gallium oxide (Ga₂O₃, Aldrich) and lithium oxide (Li₂O, Aldrich) as reagents, where 30 wt% excess lithium oxide was used to prevent lithium sublimation. If this excess lithium was not added or added in smaller quantities, the Li₅GaO₄ was not correctly synthesized (see Supporting Information²⁷). Powders were mechanically mixed and pressed. Then, a pellet was thermally treated at 500 °C for 24 h. Finally, the sample pellet was air-cooled and pulverized.

Figure 1 shows the XRD patterns of the Li₅GaO₄ sample synthesized by solid-state reaction and the same sample after the CO₂ chemisorption process (the second pattern is described



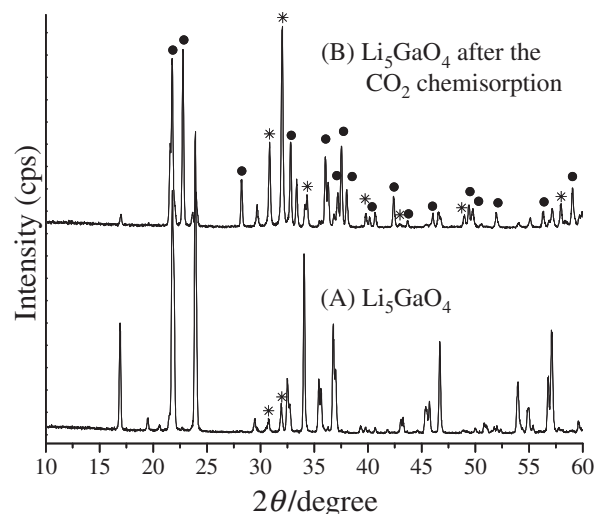


Figure 1. XRD patterns of the Li₅GaO₄ sample (A) and the Li₅GaO₄ sample after the CO₂ chemisorption process (B). Peaks labeled as * and ● correspond to Li₂CO₃ (87-0728 JCPDS card) and LiGaO₂ (72-1640 JCPDS card) compounds, respectively.

later). As it can be seen, Li₂CO₃ was detected as a secondary phase (<8%). In fact, the presence of Li₂CO₃ may indicate certain reactivity between the Li₅GaO₄ and CO₂ or the reaction of the Li₂O added in excess, as lithium carbonate was not used as reagent, and it must be produced due to the CO₂ capture of Li₅GaO₄ from the environment. In addition, the N₂ adsorption-desorption isotherm was obtained, and then the surface area of this sample was estimated using the BET model. The surface area was equal to 1 m² g⁻¹. Although the surface area is considerably small, it is comparable with the other surface areas presented by different lithium ceramics used for CO₂ capture, where the surface areas usually do not exceed 3 m² g⁻¹.^{20,21}

Once the Li₅GaO₄ was characterized, the material was thermally treated under a CO₂ flow to analyze if this material can function as CO₂ captor (CO₂ flow used was equal to 60 mL min⁻¹). If Li₅GaO₄ were able to react with CO₂, one of the following reactions may occur:



where the reaction would be similar to those observed for other lithium ceramics,^{7,10-12} in which lithium carbonate is produced in addition to a residual compound, Ga₂O₃ or LiGaO₂ in these cases. For this reaction, the maximum theoretical CO₂ capacity on Li₅GaO₄ corresponds to 14.8 (reaction 1) or 11.8 mmol g⁻¹ (reaction 2). These are smaller CO₂ absorption capacities, in comparison to the isostructural aluminium ceramic (Li₅AlO₄).

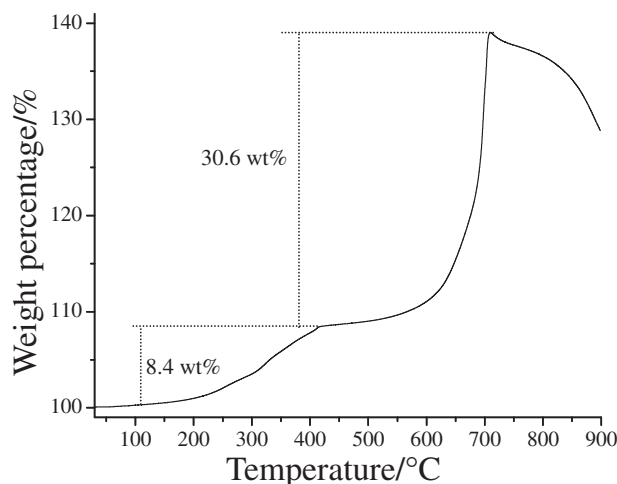


Figure 2. Dynamic thermogram analysis of the Li_5GaO_4 sample in a CO_2 flow.

Of course, this variation is simply due to the mass differences between the metal structural elements, gallium and aluminium. Therefore, the CO_2 absorption capacity of Li_5GaO_4 can be considered high among lithium ceramics and among other materials proposed for CO_2 capture.^{11,22}

Figure 2 presents the Li_5GaO_4 dynamic thermogram, where it is very clear that two different processes took place. First, between 112 and 418 °C an initial weight increment of 8.4 wt% was produced. Then, the thermogram presented a very slight increment of weight, until 568 °C, where a remarkable increment of weight was produced. Between 568 and 709 °C the sample gained 30.6 wt%. Then, the total final increment observed was equal to 39 wt%.

According to this result, Li_5GaO_4 seems to capture CO_2 in a very similar way to that observed for other lithium ceramics (Li_2O , Li_5AlO_4 , Na_2ZrO_3 , and Li_2CuO_2) presenting this reaction mechanism.^{6,11,12,23,24} First, at low temperatures, a superficial reaction is produced. At this moment, an external lithium carbonate shell is formed over the surface of the ceramic particles. Then, when the temperature is increased sufficiently and the alkaline diffusion is activated, in this case lithium, the reaction continues through the bulk of the material, completing the CO_2 capture. For Li_5GaO_4 , an identical reaction mechanism can be described. The superficial reaction corresponds to the first increment of weight observed between 112 and 418 °C. Later, at temperatures equal or higher than 568 °C the lithium diffusion should be activated and the process continued through the Li_5GaO_4 bulk. Finally, it can be seen in Figure 2 that at temperatures higher than 715 °C, the desorption process is activated. This is in good agreement with the Li_2CO_3 melting point (720 °C). In order to corroborate the reaction mechanism, the Li_5GaO_4 sample after CO_2 capture was characterized by XRD (Figure 1B). As it can be seen, different compounds were detected; Li_2CO_3 , LiGaO_2 , and Li_5GaO_4 . This result confirms that CO_2 is being trapped chemically, producing Li_2CO_3 and LiGaO_2 as products. Therefore, the reaction mechanism must correspond to that proposed in reaction 2.

Summarizing, Li_5GaO_4 was synthesized and characterized. Then, the CO_2 absorption capacity was evaluated dynamically in a thermobalance with a CO_2 flow. The results clearly showed

that Li_5GaO_4 would be considered as an alternative for CO_2 absorption. Li_5GaO_4 absorbs CO_2 in a wide range of temperatures, and the final weight increment observed in this sample was equal to 39 wt%, which corresponds to a CO_2 capture of 8.9 mmol g^{-1} . If this material is compared to other lithium ceramics, only Li_5AlO_4 has presented a higher experimental CO_2 absorption.¹¹ On the other hand, if these results are compared with the CO_2 absorption reported for other inorganic materials,^{22,25,26} such as hydrotalcites, activated carbons, earth-alkaline oxides (CaO mainly), zeolites, and organic-inorganic hybrids, it is still a good result. In general, activated carbons, zeolites, and organic-inorganic hybrid materials adsorb CO_2 between 200 and 400 °C, having the best efficiencies of ca. 6 mmol g^{-1} . Hydrotalcites absorb CO_2 at higher temperatures (450–800 °C), but their efficiencies are very poor, 2 mmol g^{-1} maximum. Finally, CaO is one of the best CO_2 captors (theoretical capacity, 17.8 mmol g^{-1}). It absorbs CO_2 between 400 and 880 °C, and the experimental efficiency has reached up to 12 mmol g^{-1} .

This work was financially supported by the projects 179-2009 ICYT-DF and IN100609-PAPIIT. Furthermore, T. Ávalos-Rendón thanks CONACYT for financial support.

References and Notes

- S. Pacala, R. Socolow, *Science* **2004**, *305*, 968.
- G. Puxty, R. Rowland, A. Allport, Q. Yang, M. Bown, R. Burns, M. Maeder, M. Attalla, *Environ. Sci. Technol.* **2009**, *43*, 6427.
- C. S. Song, *Catal. Today* **2006**, *115*, 2.
- K. Nakagawa, T. Ohashi, *J. Electrochem. Soc.* **1998**, *145*, 1344.
- K.-H. Choi, Y. Korai, I. Mochida, *Chem. Lett.* **2003**, *32*, 924.
- L. M. Palacios-Romero, H. Pfeiffer, *Chem. Lett.* **2008**, *37*, 862.
- H. Pfeiffer, P. Bosch, *Chem. Mater.* **2005**, *17*, 1704.
- X.-S. Yin, M. Song, Q.-H. Zhang, J.-G. Yu, *Ind. Eng. Chem. Res.* **2010**, *49*, 6593.
- E. Ochoa-Fernández, M. Rønning, T. Grande, D. Chen, *Chem. Mater.* **2006**, *18*, 6037.
- B. N. Nair, R. P. Burwood, V. J. Goh, K. Nakagawa, T. Yamaguchi, *Prog. Mater. Sci.* **2009**, *54*, 511.
- T. Ávalos-Rendón, J. Casa-Madrid, H. Pfeiffer, *J. Phys. Chem. A* **2009**, *113*, 6919.
- H. A. Mosqueda, C. Vazquez, P. Bosch, H. Pfeiffer, *Chem. Mater.* **2006**, *18*, 2307.
- N. Togashi, T. Okumura, K. Oh-ishi, *J. Ceram. Soc. Jpn.* **2007**, *115*, 324.
- M. Kato, K. Nakagawa, K. Essaki, Y. Maezawa, S. Takeda, R. Kogo, Y. Hagiwara, *Int. J. Appl. Ceram. Technol.* **2005**, *2*, 467.
- C. Gauer, W. Heschel, *J. Mater. Sci.* **2006**, *41*, 2405.
- T. Esaka, M. Greenblatt, *Solid State Ionics* **1986**, *21*, 255.
- A. D. Robertson, A. R. West, A. G. Ritchie, *Solid State Ionics* **1997**, *104*, 1.
- F. Stewner, R. Hoppe, *Z. Anorg. Allg. Chem.* **1971**, *380*, 241.
- F. Stewner, R. Hoppe, *Acta Crystallogr., Sect. B* **1971**, *27*, 616.
- V. L. Mejía-Trejo, E. Fregoso-Israel, H. Pfeiffer, *Chem. Mater.* **2008**, *20*, 7171.
- R. Rodríguez-Mosqueda, H. Pfeiffer, *J. Phys. Chem. A* **2010**, *114*, 4535.
- S. Choi, J. H. Drese, C. W. Jones, *ChemSusChem* **2009**, *2*, 796.
- I. Alcérreca-Corte, E. Fregoso-Israel, H. Pfeiffer, *J. Phys. Chem. C* **2008**, *112*, 6520.
- Y. Matsukura, T. Okumura, R. Kobayashi, K. Oh-ishi, *Chem. Lett.* **2010**, *39*, 966.
- Q. Wang, J. Luo, Z. Zhong, A. Borgna, *Energy Environ. Sci.* **2011**, *4*, 42.
- D. M. D'Alessandro, B. Smit, J. R. Long, *Angew. Chem.* **2010**, *49*, 6058.
- Supporting Information is available electronically on the CSJ-Journal Web site, <http://www.csj.jp/journals/chem-lett/index.html>.