

Synthesis, characterization, and crystal structure of two zinc linear dicarboxylates

Berenice Torruco Baca,¹ Luis Felipe del Castillo,¹ Paula Vera-Cruz,¹ Rubén A. Toscano,² Joelis Rodríguez-Hernández,^{1,3} and Jorge Balmaseda^{1,a)}

¹Departamento de Polímeros, Instituto de Investigaciones en Materiales, Universidad Nacional Autónoma de México, Circuito Exterior, Ciudad Universitaria, México D.F. C.P. 04510, México

²Instituto de Química, Universidad Nacional Autónoma de México, Circuito Exterior, Ciudad Universitaria, México D.F. C.P. 04510, México

³Departamento de Materiales Avanzados, Centro de Investigación en Química Aplicada, CIQA, Blvd. Enrique Reyna No. 140, C.P. 25294, Saltillo, Coahuila, México

(Received 30 June 2015; accepted 3 April 2016)

Two different crystalline structures corresponding to a zinc adipate and a zinc succinate were determined combining: X-ray powder and single-crystal diffraction, infrared spectroscopy, thermal analysis, and true densities experiments. The zinc succinate crystal structure was determined by single-crystal X-ray diffraction. This compound crystallizes in the orthorhombic space-group *Cccm* with unit-cell parameters $a = 4.792(1) \text{ \AA}$, $b = 21.204(6) \text{ \AA}$, $c = 6.691(2) \text{ \AA}$, $V = 679.8(3) \text{ \AA}^3$, and $Z = 8$. Zinc adipate crystal structure was refined from the laboratory X-ray powder diffraction data by the Rietveld method. It crystallizes in the monoclinic space group *P2/c* with unit-cell parameters, $a = 16.2037(17) \text{ \AA}$, $b = 4.7810(2) \text{ \AA}$, $c = 9.2692(6) \text{ \AA}$, $\beta = 90.329(3)^\circ$, $V = 718.07(9) \text{ \AA}^3$, and $Z = 4$. The thermal expansion of it was estimated in $5.40 \times 10^{-5} \text{ K}^{-1}$. This contribution is a step on the way to systematize the regularities in the coordination diversity between linear dicarboxylates and transition metal–inorganic buildings units of metal–organic frameworks. © 2016 International Centre for Diffraction Data. [doi:10.1017/S0885715616000221]

Key words: zinc dicarboxylate, Rietveld, crystal structure, thermal expansion

I. INTRODUCTION

The polycarboxylate anions are the precursors of a huge set of coordination polymers (Horike and Kitagawa, 2011). This abundance of compounds is because of the strength of the bonds that form, the wide range of possible O-donor ligands, and the different coordination modes they exhibit (Salles *et al.*, 2010). In the subset of aliphatic carboxylates, a large conformational freedom property must be added; which manifests itself in a variety of connection modes that yield a wide variety of architectures and topologies, many of which remain unexplored (Rao *et al.*, 2004; Sibille *et al.*, 2015; Yang *et al.*, 2015 and references therein). Some of the aliphatic carboxylates possess novel properties as adsorbents (Rao *et al.*, 2004 and references therein), molecular sieve (Rao *et al.*, 2004 and references therein), magnetic (Kim *et al.*, 2001; Rao *et al.*, 2004 and references therein; Saines *et al.*, 2012), optical (Rao *et al.*, 2004 and references therein), luminescent (Yang *et al.*, 2015), and non-linear optical materials (Jiang and Fang, 1999; Ahmad *et al.*, 2015) in addition to serving as precursors of nanoparticles (Randhawa and Gandotra, 2006). To take advantage of these properties in technological applications, it is necessary to determine the crystalline structure of the new compounds and carry out systematic crystallographic studies that will allow finding

regularities in the interaction between organic ligands and metals building units. Establishing these regularities is also possible to find correlations between metal–ligand interactions and the phase composition of the reaction products in equilibrium in order to obtain the compounds as pure as possible. In addition, the thermal evolution of these materials can be very complex, which is closely related to their properties (Saines *et al.*, 2014).

In this study, we report the syntheses, and the crystallographic, vibrational, and thermal characterizations of two zinc aliphatic dicarboxylates with molecular formulas: $[\text{Zn}_2(\text{C}_6\text{H}_8\text{O}_4)_2]$ (zinc adipate) and $[\text{Zn}_2(\text{OH})_2(\text{C}_4\text{H}_4\text{O}_4)]$ (zinc succinate). From now on, we will refer to them as ZnAdp and ZnSc, respectively. The crystal structure of ZnSc was determined from the single crystal and the thermal expansion coefficient of ZnAdp was estimated from powder diffraction patterns at 298 K and the crystal structure reported at 123 K (Klaus *et al.*, 2011).

II. EXPERIMENTAL

The coordination polymers compound were prepared by the precipitation method from aqueous solutions of zinc acetate $[\text{Zn}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 2\text{H}_2\text{O}$, Meyer Chemical Reagent grade] and adipic acid ($\text{C}_6\text{H}_{10}\text{O}_4$, Sigma-Aldrich Reagent grade), or succinic acid ($\text{C}_4\text{H}_6\text{O}_4$, Meyer Chemical $\geq 99.8\%$), with sodium hydroxide (NaOH, Hycel valued volumetric solution 1 N). In both the cases, the salt solution was added slowly

^{a)} Author to whom correspondence should be addressed. Electronic mail: balmaseda@comunidad.unam.mx

into the acid solution. The mixtures were transferred to 85 ml Teflon-lined stainless steel autoclaves for a hydrothermal treatment. The concentrations, temperature, and time of both solutions are presented in Table I. After the hydrothermal treatment, the precipitates were washed with distilled water and separated by centrifugation; finally they were slowly dried at laboratory conditions.

Infrared (IR) spectra from 4000 to 400 cm^{-1} , were obtained using a Nicolet FT-IR iS5 spectrometer in an ATR mode. Thermogravimetric analyses were carried out using a TA Instruments high-resolution (Hi-Res™) thermogravimetric analyzer, TGA 2950. The mass loss profiles of the samples studied were analyzed using the instrument control software Universal Analysis 2000 v 4.4A. The heating rate was dynamically controlled from 0.001 to 5 $^{\circ}\text{C min}^{-1}$ (instrumental resolution = 5) with an air purge rate of 62.5 ml min^{-1} . True density experiments were performed with helium in AccuPyc 1340 gas pycnometer from Micromeritics. About 0.1 cm^3 of dry powder samples were placed in the sample cup and purged with helium tenfold. Then, ten density experimental runs were carried out.

X-ray powder diffraction patterns were collected in Bragg–Brentano geometry at 298 K with $\text{CuK}\alpha_1$ radiation, Bruker (D8 Advance), with a primary graphite monochromator and a lynx-eye detector. The unit cell was previously identified and its parameters were calculated during the Miller indexes assignment with the help of TREOR and DICVOL algorithms (Werner *et al.*, 1985; Boulitf and Louer, 2004). The ZnAdp crystal structure was refined by the Rietveld method with the FullProf program (Rodríguez-Carvajal, 1993) using the reported crystal structure of this compound at 123 K (Klaus *et al.*, 2011). All non-hydrogen atoms were refined with isotropic displacement parameters (IDP) restricting its change by atom type. The zinc atoms were refined first, then oxygen and, at the end the carbon.

The X-ray diffraction (XRD) data for the ZnSc were collected at 298 K on a Bruker Smart Apex diffractometer equipped with a CCD detector maintained near -54°C and the χ -axis fixed at 54.74° . The frame data were acquired with the SMART (Bruker, 1999) software using $\text{MoK}\alpha$ radiation ($\lambda = 0.71073 \text{ \AA}$) from a fine-focus tube. Initial cell constants were determined from ninety 15-s frames. A complete hemisphere of data is scanned on omega (0.3°) with a run time of 15 s per frame at the detector resolution of 512×512 pixels. A total of 2400 frames were collected in four sets and a final set of 50 frames, identical to first 50 frames, were also collected to determine crystal decay. The frames were then processed using the SAINT software (Bruker, 2008b) to give the *hkl* file corrected for L_p/decay . Absorption corrections were applied (transmission range:

0.5533–0.7452) using the SADABS program (Bruker, 2008a). The crystal used for the diffraction study showed no decomposition during data collection. The number of measured and unique reflections was 3224 and 334, respectively, with R_{int} 0.0442. Assignment of the space group was unambiguous and the unique group *Cccm* was dictated by the systematic absences in addition with a centric intensity distribution statistics. The structure was solved by direct methods, using the SHELXS program (Sheldrick, 2008) and refined by least-squares method on F^2 , SHELXL-2014 (Sheldrick, 2008), incorporated in APEX2 suite (Bruker, 2012). All non-hydrogen atoms were refined anisotropically. Hydrogen atoms attached to C-atoms were placed in their geometrically generated positions and refined as a riding model, while those attached to O-atoms were located on a difference Fourier map at advanced refinement stage and their positional parameters refined.

III. RESULTS AND DISCUSSION

A. Vibrational analyses

The IR spectra of both precipitates do not show the characteristic bands of the precursor acid at about 1700 cm^{-1} . This confirms that the carboxylate groups in the adipate and succinate ligands are completely deprotonated. The absence of $\nu(\text{OH})$ vibration evidences that ZnAdp is anhydrous. The $\nu(\text{OH})$ vibration in ZnSc, appears as a broad signal in the region from 3430 to 3146 cm^{-1} . The widening is evidence of the existence of hydrogen bonding in the crystal structure. This signal is not very strong, suggesting the absence of water molecules.

The asymmetric $\nu_{\text{as}}(\text{CO}_2)$ and symmetric $\nu_{\text{s}}(\text{CO}_2)$ stretching vibrations are found in the region of 1600–1300 cm^{-1} . These bands are sensitive to the nature of the bonding with the metal ions; therefore, their separation is also indicative of the structure of a given carboxylate. Several rules have been established in the literature (Deacon and Phillips, 1980) to relate the coordination modes of the carboxylate groups with the separations between the bands ($\Delta\nu$). The IR spectra of ZnAdp and ZnSc show the $\nu_{\text{as}}(\text{CO}_2)$ bands at 1530 and 1534 cm^{-1} and two $\nu_{\text{s}}(\text{CO}_2)$ bands at 1445, 1400 cm^{-1} and 1403, 1385 cm^{-1} , respectively. The absorption bands shift are $\Delta = 150 \text{ cm}^{-1}$ for ZnSc and 130 cm^{-1} for ZnAdp, which is consistent with bridge bidentate syn-anti coordination mode of the carboxylates group (Deacon and Phillips, 1980). The presence of two $\nu_{\text{s}}(\text{CO}_2)$ bands in each case suggest two different bond distances in syn and anti coordinations modes of the ligand with zinc atoms. The shift in the position of the $\nu_{\text{s}}(\text{CO}_2)$ bands is associated with the difference in the chain lengths of adipate and succinate ligands.

B. Thermogravimetric analysis

Thermogravimetric curves have no thermal events at temperatures below 200 $^{\circ}\text{C}$. This behavior is consistent with the anhydrous character of the compounds observed by IR spectroscopy. A single thermal event with a weight loss of 60.55% is observed from 340 to 417 $^{\circ}\text{C}$ for ZnAdp. It was assigned to the evolution of $\text{C}_6\text{H}_8\text{O}_3$, associated with the decomposition process (expected weight loss: 61.15%). The thermal evolution is more complex in ZnSc than in ZnAdp sample.

TABLE I. Synthesis conditions and reagents used.

Sample	Concentration (M)		Temp ($^{\circ}\text{C}$)	Heating time (days)	Powder color
	Acid	Metal			
ZnAdp	0.1 ^a	0.1 ^c	150	4	White
ZnSc	0.5 ^b	0.3 ^c	110	6	White prism

^a $\text{C}_6\text{H}_{10}\text{O}_4$, Sigma-Aldrich reagent grade.

^b $\text{C}_4\text{H}_6\text{O}_4$, Meyer chemical $\geq 99.8\%$.

^c $\text{Zn}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 2\text{H}_2\text{O}$, Meyer Chemical reagent grade.

The ZnSc sample thermogravimetric curve shows two thermal events. The first starts at 209 °C up to 264 °C, where the weight loss rate approaches to zero. This tendency continues until 357 °C where the weight loss rate increases sharply due the second thermal event. This weight loss ends at 429 °C to complete a full-weight loss of 36.48%. Thermogravimetric profiles of transition metal hydroxosuccinates under oxygen atmosphere show a unique and abrupt weight loss, characteristic of the anions evolution (Livage *et al.*, 1998). A profile with two thermal events suggests the existence of impurities in the sample. The impurity prevents a quantitative analysis based on the thermogram. However, it can be assumed that the second thermal event is associated with the decomposition of ZnSc, among other events.

C. Crystal structures

The XRD analysis reveals that compounds studied exhibit very different molecular structures. Their patterns were indexed in a monoclinic (adipate) and orthorhombic (succinate) unit cell with figure of merit $M(20) > 80$ and $F(20) > 130$. Table II shows the crystal data and their cell parameters refined.

1. $Zn_2(C_6H_8O_4)_2(ZnAdp)$

The (2 0 0) and (4 0 0) reflections of ZnAdp powder pattern at 298 K are shifted with respect to the position of this peaks in the simulated powder pattern reported by Klaus *et al.* (2011) (Figure 1). The crystal structure of ZnAdp reported by Klaus *et al.*, was determined by single crystal at 123 K. The structure at 298 K was refined in the same space group $P2_1/c$ but with slight expansion of the cell volume of 0.95%. Therefore, the shifts described above could be explained based on positive thermal expansion of the material. The coefficient of isobaric thermal expansion calculated from the structures at 123 and 298 K crystallographic data is $5.40 \times 10^{-5} \text{ K}^{-1}$. The highest temperature dependence occurs in a direction. A similar behavior was observed in an isostructural cobalt adipate (Saines *et al.*, 2014).

The asymmetric unit contains one crystallographic site for: Zn(II) cation and two halves of adipate ligands [L1: C1–C3, Oc1–Oc2; L2: C4–C6, Oc3–Oc4], accommodating

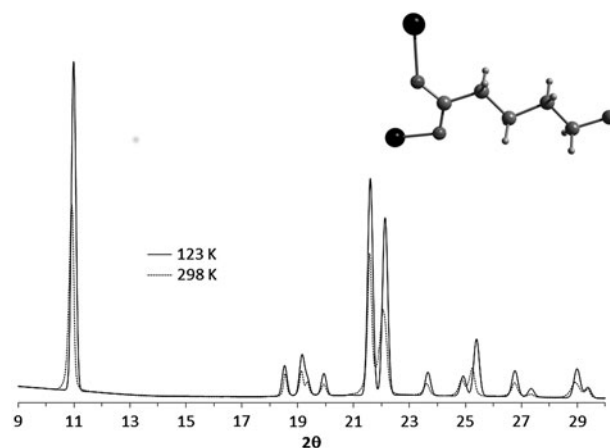


Figure 1. XRD powder patterns of ZnAdp at 298 K (dashed line) and simulated from Klaus *et al.* (2011) data at 123 K (solid line). Inset, bridge bidentate syn-anti coordination mode of the carboxylates group.

four formula units ($Z = 4$) in the unit cell. The two halves of adipate ligands L1 and L2 have the same coordination modes: bridge bidentate syn-anti as was predicted in the vibrational analysis section (Figure 1, inset). The atoms of zinc, present a tetrahedral coordination, by four oxygen atoms of adipate ligands (L1, L2). The bond distances and angles of the ZnO_4 tetrahedral and adipate ligands are very similar to those found at 123 K.

2. $Zn_2(OH)_2(C_4H_4O_4)(ZnSc)$

X-ray powder diffraction studies revealed some impurities which could not be identified. This corresponds with the results of thermal analysis.

The structure of this compound was determined by single crystal in the $Cccm$ space group. The asymmetric unit contains one crystallographically site for: Zn(II) cations (Zn), succinate ligand (L1: C1→C2, Oc1→Oc2) and hydroxyl group (Oh), accommodating eight formula units ($Z = 8$) in the unit cell. The zinc atom has a tetrahedral coordination, two oxygen atoms of different chains succinate [$Zn-Oc1 = 1.962(3)$ and $Zn-Oc2 = 1.992(3)$ Å] and two oxygen atoms of hydroxyl groups [$Zn-Oh = 1.937(2)$ Å]. Tetrahedrons are connected via the hydroxyl groups to form one-dimensional inorganic

TABLE II. Crystal data and structural refinement parameters.

	$Zn(C_6H_8O_4)$	$Zn_2(OH)_2(C_4H_4O_4)$
Molecular formula	$Zn(C_6H_8O_4)$	$Zn_2(OH)_2(C_4H_4O_4)$
Formula wt (Sum)	209.51(2)	139.42
Wavelength (Å)	1.54056	0.71073
Crystal system	Monoclinic	Orthorhombic
Space group	$P2_1/c$	$Cccm$
a (Å)	16.2037 (17)	4.792 (1)
b (Å)	4.7810 (2)	21.204 (6)
c (Å)	9.2692 (6)	6.691 (2)
β (°)	90.329 (3)	–
V (Å ³)	718.07 (9)	679.8 (3)
Z	4	8
ρ exp (g cm^{-3})	2.010 (3)	–
ρ calc (g cm^{-3})	1.93 (3)	2.724
R_p	9.93	2.46
R_{wp}	10.4	5.78
R_{exp}	2.14	–
S	4.85	1.155

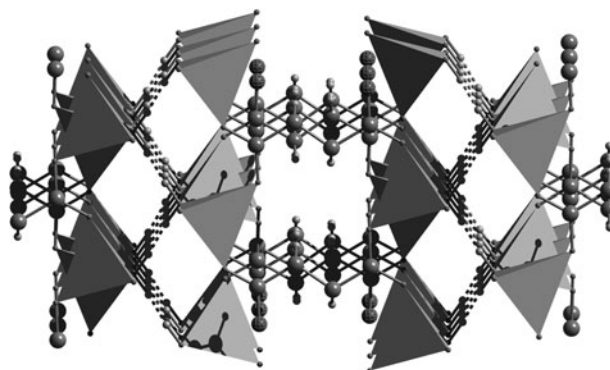


Figure 2. Layers of ZnO_4 tetrahedra chains connected by succinate ligands interacting with each other by hydrogen bond in $2 \times 1 \times 2$ supercell of ZnSc. View in the c -direction. The oxygen atoms are represented in globe style.

chains [$Zn \cdots Zn = 4.792$ (2) Å] parallel to the axis c (Figure 2). Carboxylates succinate anions exhibit the bridge bidentate coordination, allowing the carbon atoms of ligand act as pillars [$Zn \cdots Zn = 7.117$ (2) Å] between chains ZnO_4 . The resulting framework is a polymer sheets linked by hydrogen bonds [$Oh \cdots Oh = 2.869$ (3) Å] through the hydroxyl groups.

Solvent accessible voids in crystal structures of ZnAdp and ZnSc calculated by PLATON (Spek, 2009) were null for probes radius greater than 1 Å. These estimations were confirmed experimentally by CO_2 adsorption at 273.15 K up to 1 atm.

SUPPLEMENTARY DATA

Infrared spectra and thermogravimetric curves of ZnAdp and ZnSC, an image of the crystal structure of ZnAdp, atomic positions, bonds distances, and angles for the structure of both compounds are supplied as supplementary information.

SUPPLEMENTARY MATERIAL

To view supplementary material for this article, please visit <http://dx.doi.org/10.1017/S0885715616000221>.

ACKNOWLEDGEMENTS

This research was partially supported by the Projects: CONACyT 154626, CONACyT-CNPq 174247, SECITI-CLAF 025/2014, and DAGAPA-PAPIIT IG-100315. SENER-117373, CONACyT-CB2007-82964. The authors thank Damaris Cabrero Palomino and Adriana Tejada Cruz for their technical assistance.

- Ahmad, N., Ahmad, M. M., and Kotru, P. N. (2015). "Single crystal growth by gel technique and characterization of lithium hydrogen tartrate," *J. Cryst. Growth* **412**, 72–79.
- Boultif, A. and Louer, D. (2004). "Powder pattern indexing with the dichotomy method," *J. Appl. Crystallogr.* **37**(5), 724–731.
- Bruker (1999). *SMART, Software for the CCD Detector System, version 5.625 (Computer Software)* (Bruker AXS, Inc., Madison, Wisconsin, USA).
- Bruker (2012). *APEX2 (Computer Software)* (Bruker AXS, Inc., Madison, Wisconsin, USA).
- Bruker (2008a). *SADABS, Area Detector Scaling and Absorption Correction, version 2008/1 (Computer Software)* (Bruker AXS, Inc., Madison, Wisconsin, USA).
- Bruker (2008b). *SAINT, Software for the CCD Detector System, version 7.34 (Computer Software)* (Bruker AXS, Inc., Madison, Wisconsin, USA).

- Deacon, G. B. and Phillips, R. J. (1980). "Relationships between the carbon–oxygen stretching frequencies of carboxylato complexes and the type of carboxylate coordination," *Coord. Chem. Rev.* **33**(3), 227–250.
- Horike, S. and Kitagawa, S. (2011). "Design of porous coordination polymers/metal–organic frameworks: past, present and future," in *Metal–Organic Frameworks: Applications from Catalysis to Gas Storage* (ed David Farrusseng), Wiley–VCH Verlag GmbH & Co. KGaA, Weinheim, Germany.
- Jiang, M.-h. and Fang, Q. (1999). "Organic and semiorganic nonlinear optical materials," *Adv. Mater.* **11**(13), 1147–1151.
- Kim, Y. J., Jung, D.-Y., Hong, K.-P., and Demazeau, G. (2001). "Solid solution of transition metal–dicarboxylates with tunable magnetic properties," *Solid State Sci.* **3**(8), 837–846.
- Klaus, S., Lehenmeier, M. W., Herdtweck, E., Deglmann, P., Ott, A. K., and Rieger, B. (2011). "Mechanistic insights into heterogeneous zinc dicarboxylates and theoretical considerations for CO_2 –epoxide copolymerization," *J. Am. Chem. Soc.* **133**(33), 13151–13161.
- Livage, C., Egger, C., Nogues, M., and Férey, G. (1998). "Hybrid open frameworks (MIL- n). Part 5 Synthesis and crystal structure of MIL-9: a new three-dimensional ferrimagnetic cobalt(II) carboxylate with a two-dimensional array of edge-sharing Co octahedra with 12-membered rings," *J. Mater. Chem.* **8**(12), 2743–2747.
- Randhawa, B. and Gandotra, K. (2006). "A comparative study on the thermal decomposition of some transition metal carboxylates," *J. Therm. Anal. Calorimetry* **85**(2), 417–424.
- Rao, C. N. R., Natarajan, S., and Vaidhyanathan, R. (2004). "Metal carboxylates with open architectures," *Angew. Chem. Int. Ed.* **43**(12), 1466–1496.
- Rodríguez-Carvajal, J. (1993). "Recent advances in magnetic structure determination by neutron powder diffraction," *Phys. B: Condens. Matter* **192** (1–2), 55–69.
- Saines, P. J., Barton, P. T., Jain, P., and Cheetham, A. K. (2012). "Structures and magnetic properties of Mn and Co inorganic–organic frameworks with mixed linear dicarboxylate ligands," *CrystEngComm* **14**, 2711–2720.
- Saines, P. J., Barton, P. T., Jura, M., Knight, K. S., and Cheetham, A. K. (2014). "Cobalt adipate, $Co(C_6H_8O_4)$: antiferromagnetic structure, unusual thermal expansion and magnetoelastic coupling," *Mater. Horiz.* **1**, 332–337.
- Salles, F., Maurin, G., Serre, C., Llewellyn, P. L., Knöfel, C., Choi, H. J., Filinchuk, Y., Oliviero, L., Vimont, A., Long, J. R., and Férey, G. (2010). "Multistep N_2 breathing in the metal–organic framework $Co(1,4\text{-benzenedipyrzolate})$," *J. Am. Chem. Soc.* **132**(39), 13782–13788.
- Sheldrick, G. M. (2008). "A short history of SHELX," *Acta Crystallogr. A* **64** (1), 112–122.
- Sibille, R., Mazet, T., Malaman, B., Wang, Q., Didelot, E., and François, M. (2015). "Site-dependent substitutions in mixed-metal metal–organic frameworks: a case study and guidelines for analogous systems," *Chem. Mater.* **27**(1), 133–140.
- Spek, A. (2009). "Structure validation in chemical crystallography," *Acta Crystallogr. D* **65**(2), 148–155.
- Werner, P.-E., Eriksson, L., and Westdahl, M. (1985). "TREOR, a semi-exhaustive trial-and-error powder indexing program for all symmetries," *J. Appl. Crystallogr.* **18**(5), 367–370.
- Yang, J. X., Qin, Y.-Y., Cheng, J.-K., Zhang, X., and Yao, Y.-G. (2015). "Construction of a series of Zn(II) compounds with different entangle motifs by varying flexible aliphatic dicarboxylic acids," *Cryst. Growth Des.* **15**(5), 2223–2234.