



# Keratin fibres derived from tannery industry wastes for flame retarded PLA composites



Guadalupe Sanchez-Olivares <sup>a,\*</sup>, Antonio Sanchez-Solis <sup>b</sup>, Fausto Calderas <sup>a</sup>, Jenny Alongi <sup>c</sup>

<sup>a</sup> CIATEC, A.C., Omega 201, 37545 León, Gto., Mexico

<sup>b</sup> Instituto de Investigaciones en Materiales, Universidad Nacional Autónoma de México, Avenida Universidad 3000, 04510 Ciudad de México, Mexico

<sup>c</sup> Dipartimento di Chimica, Università degli Studi di Milano, Via Golgi 19, 20133 Milan, Italy

## ARTICLE INFO

### Article history:

Received 20 December 2016

Received in revised form

31 March 2017

Accepted 9 April 2017

Available online 13 April 2017

### Keywords:

Keratin fibres

Flame retardant

Thermal stability

PLA

Tannery wastes

## ABSTRACT

In this work, keratin fibres (KFs) were recovered from tannery industry wastes and reused for preparing completely green materials based on poly(lactic acid) (PLA) composites. A specific process for extracting and treating KFs as reinforcing and flame retardant agents for PLA was used. KFs were characterised by scanning electron microscopy, thermogravimetric analysis (TGA) and total nitrogen content by Kjeldahl method. PLA was compounded using both KFs at different contents and KFs in combination with a traditional flame retardant, namely, aluminium trihydroxide (ATH), in order to exploit the joint action between these two species. PLA composites were studied by scanning electron microscopy, thermogravimetry in nitrogen and air, UL94 classification, dynamical-mechanical, mechanical and rheological measurements. As a result, a good KF/polymer matrix adhesion was observed. Thus, PLA passes from V2 with only KFs (3 phr) to V0 classification when KFs are added in combination with 30 phr ATH. Tensile strength was increased by 16%, strain at break by 40% and tenacity by 66% when ATH content was reduced from 50 phr to 30 phr in joint combination with 3 phr KF content. Rheological measurements in simple and oscillatory shear flows showed that KFs reduced the viscosity of the investigated materials, improving the processability of composites.

© 2017 Elsevier Ltd. All rights reserved.

## 1. Introduction

As it is well known, the industrial and agriculture activities produce a considerable waste amount, mainly concerning the high volumes of fibres and fibrous materials. Several efforts have been carried out in the world in order to reduce such problem. However, the high cost of the specific treatments for fibres, processing difficulties and development of desired properties for producing useful products are still the main issues to consider when preparing materials reinforced with fibres from industrial wastes [1,2]. A great number of investigations have been published in the polymeric materials research area on natural fibres as reinforcing agents from the agriculture industry for over 40 years. These reports have been focused on cellulosic fibres as biofibres due to their positive environmental impact, non-abrasive properties, economical production

and low specific weight [3,4]. As an example, cellulosic composites have been extensively used in the automotive industry for producing fibre-reinforced composite polymeric materials ever since 1957 [3,5,6]. The properties of these composites (natural fibre/polymer matrix) depend on different parameters such as fibre type, content, pre-treatment, fibre/polymer matrix compatibility and processing [7–9]. As far as fibres derived from animals are considered, in the last decade, both industrial and academic researchers have paid a great attention to keratin fibres (KFs) from poultry feathers. Indeed, it has been found that KFs can effectively act as reinforcing agent for polymers, increasing their Young's modulus, tensile strength, flexural modulus, and hardness. KFs have also reported to increase polymer thermal stability better than cellulosic fibres [10–12].

On the other hand, tannery industry is a high pollutant emission sector. The wastes derived from this sector have a strong negative environmental impact due to the high content of the organic matter in the effluents or solids [13]. During tannery leather process, the beamhouse stage is the first step to tanner leather; in this stage different operations are involved; one of them is the *liming* step that requires several alkaline products, which chemically attack the

\* Corresponding author.

E-mail addresses: [gsanchez@ciatec.mx](mailto:gsanchez@ciatec.mx) (G. Sanchez-Olivares), [sancheza@unam.mx](mailto:sancheza@unam.mx) (A. Sanchez-Solis), [fcalderas@ciatec.mx](mailto:fcalderas@ciatec.mx) (F. Calderas), [jenny.alongi@unimi.it](mailto:jenny.alongi@unimi.it) (J. Alongi).

keratin, causing skin swelling and hair detaching. From this operation, the wastes are handed as slurry, and then separated in solid and liquid parts. Sometimes the hair is partially removed through a mechanical operation halfway through the liming operation and it is thrown in sanitary fills [14,15]. However, wasted hair is considered an important keratin fibre source that can potentially have important applications in polymer materials.

To the best of our knowledge, in the literature there are no published papers on the use of KFs derived from tannery industry wastes as reinforcing and flame retardant agent in polymeric composites. Considering that poly(lactic acid) (PLA) is one of the main biopolymers produced and commercialized up to now, its applications are being addressed to different fields where flame retardant properties are required [16]. Thus, PLA/KF composites might be valuable and potentially green materials.

In this context, the present work assesses the potential of keratin fibres derived from tannery industry waste as both: flame retardant and reinforcing agent for PLA. A specific conditioning treatment for KFs was carried in order to make them suitable for the extrusion with PLA. The effect of keratin fibre content as well as the joint action with a halogen-free flame retardant (namely, ATH) on morphology, thermal stability, flame retardant, dynamic-mechanical, mechanical and rheological properties of the resulting materials was thoroughly investigated.

## 2. Experimental part

### 2.1. Materials

Poly(lactic acid) (PLA) INGENO 3251D was purchased from NatureWorks LLC; keratin fibres (KFs) were extracted as waste from Mexican tannery industry, fibre length of 1–5 mm, measured with a stereomicroscope Nikon SMZ 1270; aluminium trihydroxide (ATH), industrial grade (99.5% purity), particle sizes of 1.0–2.5  $\mu\text{m}$  and surface area of 12  $\text{m}^2/\text{g}$  was supplied by ABAQUIM, Mexico.

### 2.2. Keratin fibre treatment

As mentioned above, KFs (derived from hair skin bovine) were obtained from the slurry of by-products from the beamhouse stage during the tannery process of the Mexican industry. The slurry was rinsed and delimed in order to reduce the high alkalinity produced in the liming stage and degreased, these steps were carried out using tannery test drums. After degreasing, keratin fibres were dried initially outdoor and then in an oven at 40 °C for 12 h.

The total nitrogen content within keratin fibres (the main component) was assessed by Kjeldahl method. Briefly, this method consists in digesting sample in sulphuric acid, which converts nitrogen-based compounds (mainly, proteins, amines, organic compounds) into ammonia. Then, free ammonia is released by the addition of caustics, which are then expelled by distillation and subsequently titrated [17]. The result of such analysis on KFs employed in the present study was 91.0% total nitrogen in protein form.

### 2.3. Preparation of PLA composites by extrusion

PLA composites were obtained by extrusion process by using a twin-screw counter-rotating Leistritz Micro 27 extruder, L/D = 32 and 27 mm diameter with 8 heating zones. The counter-rotating intermeshing extruder was used because the compounding is forced to pass between two screws increasing pumping and melt pressure towards the die. In industry, co-rotating intermeshing is generally preferred by the higher output rate. Before extrusion, neat PLA was dried under vacuum, the operating pressure during

the heating stage was 80 psi (0.5516 MPa) and 110 °C for 30 min. In order to investigate the flame retardant effect of KFs on PLA, a reference sample using high traditional flame retardant additive content was prepared (namely, PLA\_ATH<sub>50</sub> sample). Samples with different KF content and samples using both KFs and ATH were prepared, as well. All materials were compounding under a temperature profile 165/165/175/175/185/185/190 °C at 100 rpm rotational speed. Table 1 describes the composition of investigated materials.

### 2.4. Preparation of PLA sample by injection moulding

Samples for flammability (125 mm × 13 mm × 3 mm), mechanical (specimen sizes according to the type I, thickness 3.1 mm ± 0.1 described in the ASTM D638 standard) and dynamic-mechanical (60 mm × 13 mm × 3 mm) tests were obtained in an injection moulding machine Milacron TM55 model under the following conditions: 175/185/190/180 °C temperature profile, 70 mm/s injection speed, 110 bar injection pressure and 20 s cooling time. All materials were dried under vacuum before being processed by injection moulding under the same conditions as those used for processing PLA by extrusion.

### 2.5. Characterization

The morphology of PLA and corresponding materials was studied using a JEOL JSM-7600F Scanning Electron Microscope (SEM). Fractured pieces were gold-metallized in order to make them conductive. Flame retardant properties were assessed following the UL94 classification in vertical configuration according to the ASTM D3801 standard [18]. Mechanical tests were carried out using a tensile Instron machine 5565 at 50 mm/min crosshead speed, following the ASTM D638 standard [19]. Thermogravimetric analysis (TGA) was carried out in a TA-Instrument Q5000 IR Discovery calorimeter under a heating rate of 10 °C/min in nitrogen and air atmospheres; the experimental error was ±1 °C and ±0.01 wt.-%. Temperatures at 10 wt.-% loss ( $T_{10\%}$ ), at maximum weight loss ( $T_{\text{max}}$ ) and final residues at 600 °C were assessed. Rheological measurements were performed in a stress-controlled TA-Instrument G2 rheometer using parallel-plates (25 mm diameter); all tests were carried out at the temperature of 190 °C and gap of 0.75 mm, under Small Amplitude Oscillatory Shear flow (SAOS) measurements. The oscillatory tests were performed in linear viscoelastic regime (5% strain). Dynamic-mechanical analysis were carried out in a TA-Instrument Q800 analyser with a frequency of 1.0 Hz, amplitude of 10  $\mu\text{m}$  and heating speed of 3 °C/min using a dual cantilever geometry at 30–110 °C temperature range; storage modulus ( $E'$ ) was assessed and the experimental modulus error was ±1%.

**Table 1**  
Formulations.

Sample	KF content [phr]	KF content [wt.-%]	ATH content [phr]	ATH content [wt.-%]
PLA	–	–	–	–
PLA_ATH <sub>50</sub>	–	–	50	33.3
PLA_ATH <sub>30</sub>	–	–	30	23.1
PLA_KF <sub>10</sub>	10	9.1	–	–
PLA_KF <sub>5</sub>	5	4.8	–	–
PLA_KF <sub>3</sub>	3	2.9	–	–
PLA_KF <sub>10</sub> /ATH <sub>30</sub>	10	7.1	30	21.4
PLA_KF <sub>5</sub> /ATH <sub>30</sub>	5	3.7	30	22.1
PLA_KF <sub>3</sub> /ATH <sub>30</sub>	3	2.2	30	22.2

### 3. Results and discussion

#### 3.1. Morphology

Fig. 1 displays the SEM micrographs of the fractured surfaces for PLA (A), KFs (B), PLA\_KF<sub>10</sub> (C) and PLA\_KF<sub>10</sub>/ATH<sub>30</sub> composites (D). According to the micrograph reported in Fig. 1A, PLA exhibits a fragile fracture, since fracture planes are well defined, characterised by flat surfaces and no deformation is visible; thus, the observed morphology is characteristic of rigid and fragile materials. Fig. 1B depicts a typical morphology of KFs [20–22]: fibres with cylindrical shape having a diameter of approximately 43  $\mu\text{m}$  and characterised by overlapped layers on the surface (cuticle) are observable. In order to study keratin fibre morphology, several micrographs were taken (see Figs. S1–S5 included in the Supplementary Material), same cylindrical shapes with different fibre diameters from 16 up to 83  $\mu\text{m}$  (43  $\mu\text{m}$ , average diameter) were observed; this variability can be ascribed to the natural source of KFs (hair skin bovine).

The morphology of PLA loaded with KFs (10 phr) is reported in Fig. 1C; KFs lie in different fractured planes with respect to the matrix, without interstices between keratin fibre and polymer; the above morphology suggests that such fibres is likely to act as

mechanical reinforcement for PLA. When ATH is added to the formulation (namely, PLA\_KF<sub>10</sub>/ATH<sub>30</sub> sample), no interstices around fibre and good adhesion between keratin fibres and polymer matrix are clearly observed (see Fig. 1D). According to this finding, it is reasonable that KFs have somewhat chemical or physical interactions with PLA matrix, regardless of the ATH presence.

Fig. 2 shows PLA\_KF<sub>10</sub>/ATH<sub>30</sub> morphology in a different point with respect to that reported in Fig. 1D at 500 $\times$  magnification; it is interesting to observe that KF surface is homogeneously coated by the polymer (pointed out by white arrows) and fibres appear embedded within the matrix; no empty holes caused by the fibre pull out are observed. According to the observed morphologies, KFs exhibit a very good adhesion with polymer, probably due to the hydrophobic feature with high aspect ratio typical of KFs; therefore chemical or physical bonds can be possible, as already stated and observed in the literature [23,24].

#### 3.2. Thermal stability

Thermal properties of keratin fibres were assessed and compared with those of ATH by TGA under nitrogen and air. Fig. 3

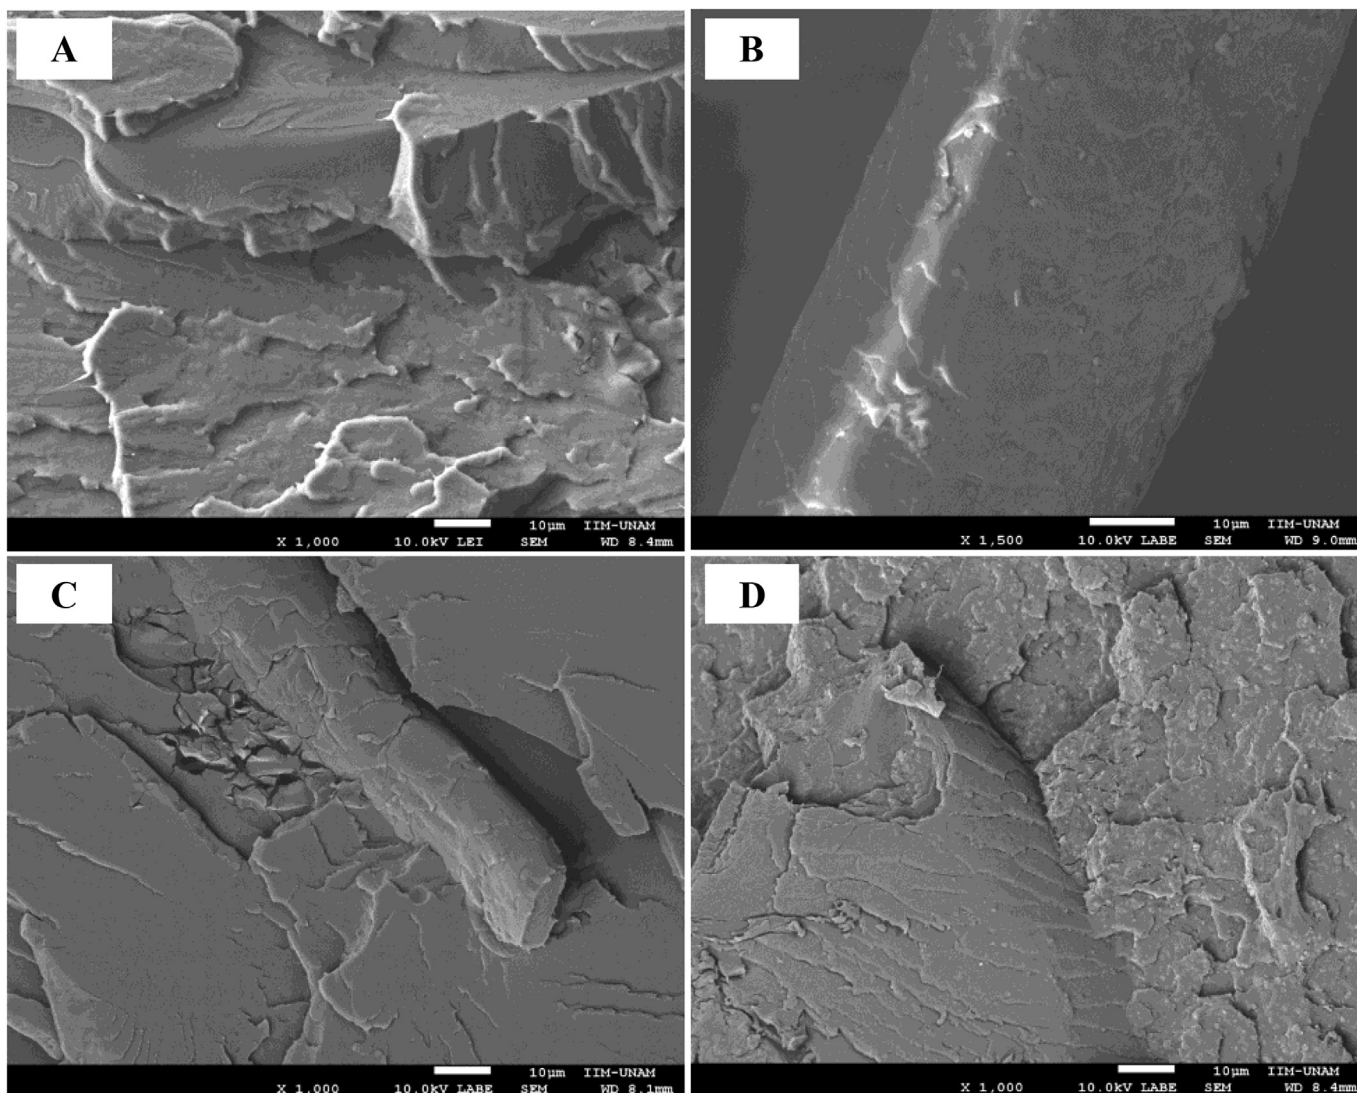


Fig. 1. SEM micrographs of A) Neat PLA (1000X) and B) KF (1500X), C) PLA\_KF<sub>10</sub> (1000X) and D) PLA\_KF<sub>10</sub>/ATH<sub>30</sub> (1000X) composites.

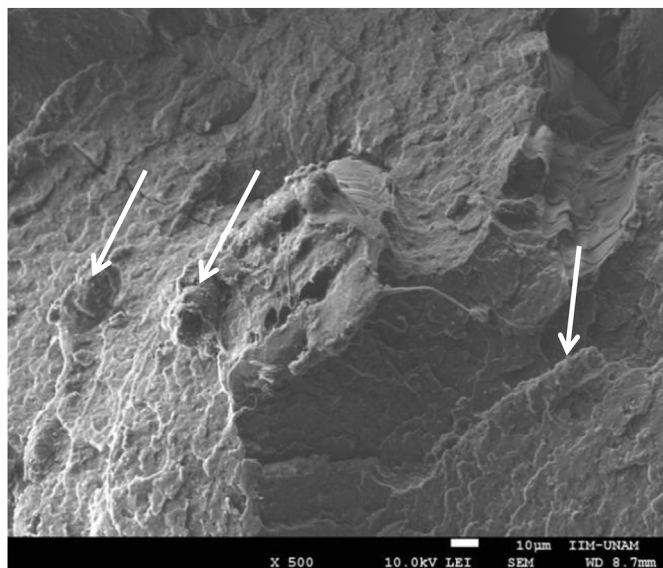


Fig. 2. SEM micrograph of PLA\_KF10/ATH30 composite at 500X.

displays the weight loss as a function of temperature under nitrogen atmosphere (TG and dTG curves in A and B, respectively) and Table 2 discloses the collected data.

According to Fig. 3, KFs lose 10% weight (Fig. 3A) at 233 °C ( $T_{10\%}$  in Table 2). The main degradation step occurs at 304 °C ( $T_{max}$ , see dTG curve in Fig. 3 and Table 2); at that point, the weight loss rate is 0.58%/°C. Meanwhile at 282 °C ATH shows its main degradation step ( $T_{max}$ ) with a weight loss rate of 0.79%/°C. At 600 °C, KFs and ATH left 24.2 and 65.8% of final residue, respectively.

In air (Fig. 4 and Table 2), the main degradation of KFs undergoes two steps, the former with a  $T_{max}$  of 340 °C (with 0.43%/°C weight loss rate) and the latter at 556 °C (with 0.51%/°C weight loss rate). In the meantime, ATH degrades in air by a single step having a  $T_{max}$  of 313 °C, with 0.87%/°C weight loss rate.

According to the collected data by TGA, KFs have proven to be thermally stable both in nitrogen and air. This finding is probably due to its chemical structure; indeed, keratin is a protein with a complex quaternary structure rich of amino acids and disulphide bonds that upon heating releases volatile species such as  $NH_3$ ,  $CO_2$ , and  $SO_2$  as well as produces  $H_2S$  able to induce the formation of phenol-based compounds at approximately 300 °C. The latter compounds are thermally stable structures at very high temperatures [25]. This behaviour seems to be a specific feature of some proteins such as whey proteins, caseins and hydrophobins, as already demonstrated [26–29].

As far as PLA and KF-based composites are concerned, Figs. 5 and 6 reports the TG (A) and dTG (B) curves in nitrogen and air, respectively.

In nitrogen, neat PLA degrades through a single decomposition step, without leaving any residue at 600 °C. Indeed, 0.3% reported in Table 3 can be considered negligible, taking into account the experimental error on weight in TGA (see Experimental Part).

The presence of KFs, regardless their content (namely, 3, 5 or 10 phr), significantly anticipates PLA thermal degradation, as well evidenced comparing the  $T_{10\%}$  values reported in Table 3. In spite of this, PLA/KF  $T_{max}$  remains almost constant and KFs induce the formation of a final residue at 600 °C that is a function of their content in composite. KFs reduce the weight loss rate with respect to neat PLA; PLA\_KF3, PLA\_KF5 and PLA\_KF10 formulations showed

weight loss rates of 2.3, 2.3 and 2.1%/°C, respectively which are significantly lower than that of PLA, namely 2.6%/°C (Fig. 5B). When only ATH is added to polymer matrix (PLA\_ATH50 and PLA\_ATH30), the anticipation of PLA degradation is more evident, 316 and 310 °C for PLA\_ATH50 and PLA\_ATH30, respectively; as compared to 369 °C for neat PLA, but at the same time ATH favours the formation of a residue at  $T_{max}$  (23.3 and 16.5%) that is thermally stable up to 600 °C (Fig. 5A). The addition of ATH also contribute to reduce the weight loss rate: namely, 2.1 and 2.2 vs. 2.6%/°C for PLA\_ATH50, PLA\_ATH30, and PLA, respectively (Fig. 5B).

The KF/ATH formulations (PLA\_KF10/ATH30, PLA\_KF5/ATH30 and PLA\_KF3/ATH30) exhibited an analogous behaviour to those samples containing only ATH (PLA\_ATH50 and PLA\_ATH30) in terms of  $T_{max}$  and  $T_{10\%}$ . However, KF/ATH formulations showed lower weight loss rate than PLA and PLA/ATH formulations (Fig. 5B). As an example, when KFs are added at the lowest content (PLA\_KF3/ATH30), the weight loss rate is 1.6%/°C, significantly lower than those of PLA, PLA\_ATH50 and PLA\_ATH30 (2.6, 2.1 and 2.2%/°C, respectively).

Thermal analysis in nitrogen has pointed out that the KF presence in combination with ATH exhibited similar thermal stability in terms of  $T_{10\%}$  and  $T_{max}$  with respect to the reference sample (PLA\_ATH50) and even lower weight loss rate.

In air (Fig. 6) the thermo-oxidation of PLA and composites occurred through a single step, similarly to what observed in nitrogen (compare Figs. 5A and 6A). Once again, the presence of KFs in combination with ATH, regardless of their content, promotes the anticipation of PLA degradation as well as the formation of a thermally stable residue at 600 °C. This behaviour is ascribed to the ATH presence, since  $T_{max}$  for PLA\_ATH50 and PLA\_ATH30 was 344 and 304 °C, respectively. Meanwhile, when KFs are added without ATH,  $T_{max}$  values were 395, 395 and 385 °C (PLA\_KF10, PLA\_KF5 and PLA\_KF3).

With respect to weight loss rate in air (Fig. 6B), the lowest value was observed in PLA\_ATH50 composite (1.5%/°C). Similar results were showed when KFs is added in combination with ATH (1.7, 1.7 and 1.8%/°C for PLA\_KF10/ATH30, PLA\_KF5/ATH30, PLA\_KF3/ATH30, respectively).

According to Fig. 6 and Table 3 (TGA in air), the thermal stability of formulation containing KFs in combination with ATH is nearly similar to that of PLA\_ATH50 in terms of  $T_{max}$  and weight loss rate.

### 3.3. Flammability

Flammability of PLA and KF-based composites was assessed in terms of resistance to a flame application in vertical configuration, following the UL94 classification. Table 4 summarises the collected data. In detail, neat PLA is a high flammable material resulting as not classifiable in UL94 classification (NC in Table 4). Indeed, during combustion, PLA vigorously burns with intense dripping; by this way, flaming drops ignite cotton. The observed behaviour does not allow PLA passing such test and to reach the highest performances (namely, V0 classification).

In order to investigate the effect of KFs on flammability of PLA composites, reference samples, namely, PLA\_ATH50 and PLA\_ATH30 were tested, as well. Indeed, according to the collected results and published in the literature [30], PLA\_ATH50 has been classified as V0 and PLA\_ATH30 as V2. These results show the high content of ATH that is required to reduce flammability properties of PLA.

When KFs are used as flame-retardants for PLA at different contents (3, 5 and 10 phr), the corresponding materials have proven to be classified as V2 (Table 4). These results indicate that KFs can be used at low content (3 phr) for reducing PLA flammability, analogously to what occurs using 30 phr ATH, even though the highest performances (V0 classification) are not reached. Higher flame

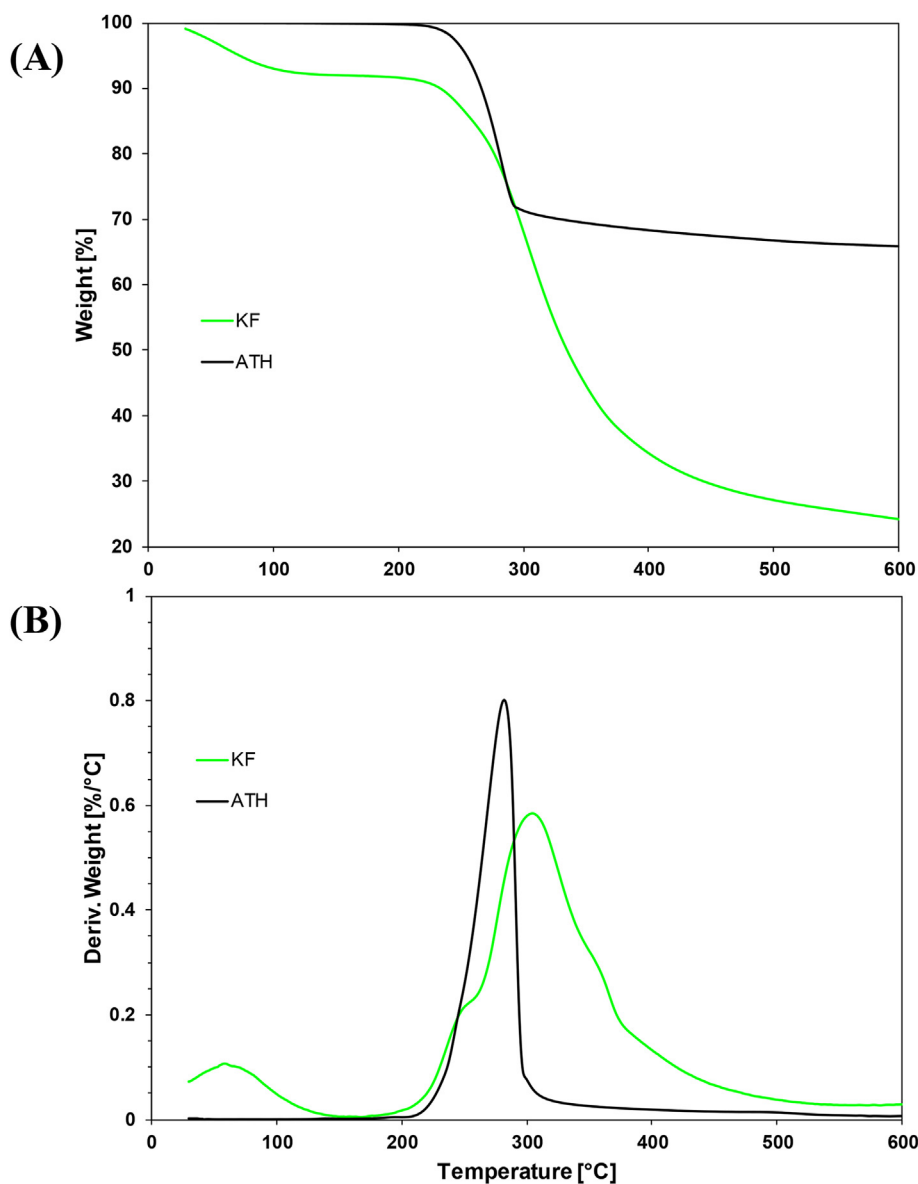


Fig. 3. TG (A) and dTG (B) curves of KFs and ATH in nitrogen.

**Table 2**

TGA data of neat KFs and ATH in nitrogen and air.

Sample	Nitrogen			Air		
	$T_{10\%}$ [°C]	$T_{max}^a$ [°C]	Residue at 600 °C [%]	$T_{10\%}$ [°C]	$T_{max}^a$ [°C]	Residue at 600 °C [%]
KFs	233	304	24.2	220	340, 556	7.0
ATH	266	282	65.8	301	313	65.8

<sup>a</sup> From derivative curves (Figs. 3B and 4B).

retardant levels have been found when KFs were combined with ATH in new formulations having the advantage to contain a lower amount of ATH with respect to the reference (30 vs. 50 phr, Table 1). Regardless of KF content, PLA<sub>KF10</sub>/ATH<sub>30</sub>, PLA<sub>KF5</sub>/ATH<sub>30</sub> and PLA<sub>KF3</sub>/ATH<sub>30</sub> composites reached V0 classification.

Fig. 7 displays some digital pictures of the samples tested following the UL94 classification; more precisely, pictures in Fig. 7A–C refer to composites containing 10, 5 and 3 phr content of KFs and Fig. 7D–F to composites containing the same KF content with 30 phr of ATH. It has been observed that the samples

containing KFs without ATH exhibited a more intense phenomenon of dripping with respect to the counterparts containing also ATH or only ATH (Fig. 7G and H). As far as PLA flame retardancy is concerned, Bourbigot and Fontaine reviewing several papers on flame retardancy of PLA [16] concluded that ATH acts as efficient flame retardant i) by diluting flammable compounds released by PLA in the gas phase, ii) by partially absorbing the combustion heat for promoting its dehydration with consequent water vaporisation, as well as iii) by forming an insulating layer of Al<sub>2</sub>O<sub>3</sub>.

Regarding the flame retardant mechanism conceivable for KFs, it

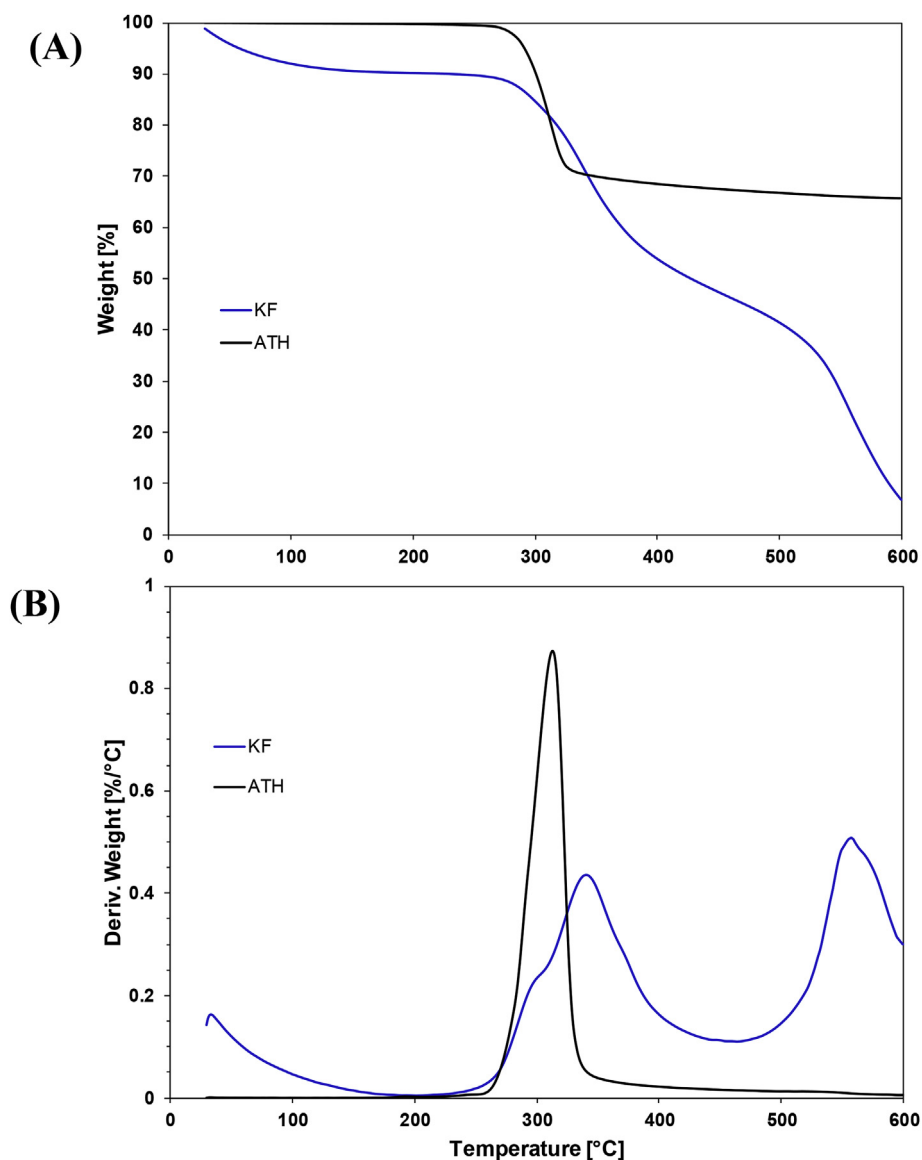


Fig. 4. TG (A) and dTG (B) curves of KFs and ATH in air.

is well known that wool has inherent low flammability, due to the high nitrogen and sulphur content in the amino acid skeleton, disulphide bonds and crosslinking level between adjacent chains [31]. An analogous mechanism and similar conclusions have been proposed for the combustion of KFs derived from poultry feathers due to their chemical structure and amino acid type and content [32,33]. According to these statements and to the flammability data reported in Table 4, it is reasonable to ascribe a similar action mechanism also to KFs from tannery industry.

Comparing the flame retardant properties achieved by using KFs, derived from tannery industry wastes, and other natural fibres in polymer composites, some previous research works have pointed out that milled keratin fibres obtained from poultry feathers in elastic polyurethane foams (10 and 16% of KF content) improved their limiting oxygen index (LOI) values and reduced the burning rate in horizontal position test [32]. Coconut fibres (10 phr) in combination of aluminium trihydrate (30 phr) in a starch-based biocomposite, reduced the burning rate according to UL94 horizontal position test and slightly increased the LOI value [33]. Ramie fibres combined with ammonium polyphosphate (APP) at 40 wt.%

in PLA composites showed V0 in UL94 classification and an increased LOI value [16].

From an overall consideration, the results collected here employing KFs have demonstrated their higher potentialities as flame retardant agents for PLA composites even at low content (3phr) with respect to the other fibres.

#### 3.4. Dynamic-mechanical behaviour

Fig. 8 displays the storage modulus ( $E'$ ) as a function of temperature for neat PLA and investigated composites. Both PLA and composites show a remarkable transition from glass to viscoelastic zone in 55–70 °C range.  $E'$  under glass transition temperature (30 °C) is strongly depending on ATH content: namely, for the composite having the highest ATH content, the highest  $E'$  was measured (6082 vs. 3810 MPa for PLA\_ATH<sub>50</sub> and PLA, respectively). The value for the composite with 30 phr ATH was 5492 MPa. The composites containing 30 phr ATH with different KF content, 10, 5 and 3 phr, showed values 5372, 5132 and 5225 MPa, respectively, that are slightly lower than that containing only ATH (5492 MPa).

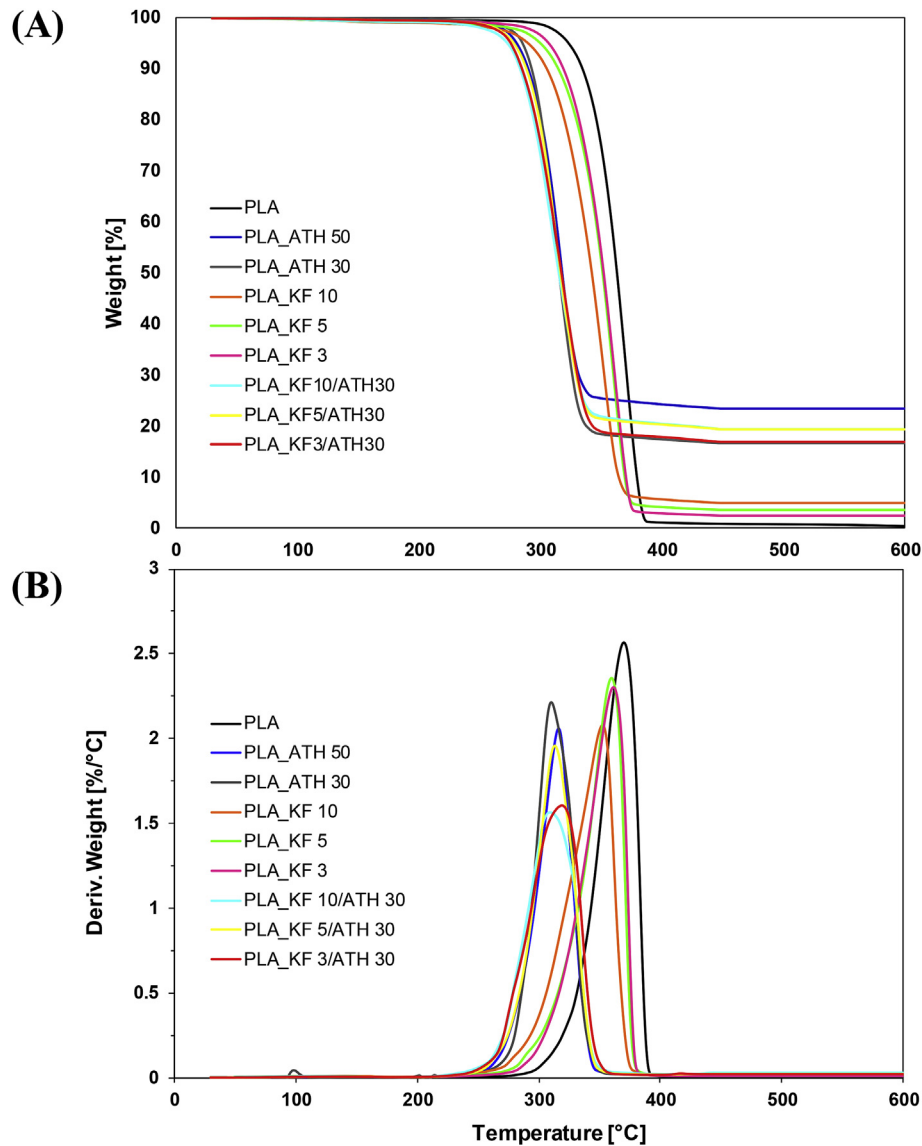


Fig. 5. TG (A) and dTG (B) curves of neat PLA and composites with KFs and ATH in nitrogen.

KF amounts did not show a significant effect on  $E'$ , particularly at low loadings.

The storage modulus showed values of 4291, 3803 and 3934 MPa when 10, 5 and 3 phr KFs are added (PLA\_KF<sub>10</sub>, PLA\_KF<sub>5</sub>, PLA\_KF<sub>3</sub>). These results point out that ATH content determines the tendency to store energy below glass transition temperature ( $T_g$ ); therefore, composites containing ATH exhibit higher stiffness with respect to composites with only KFs. This trend is in agreement with that already observed in the literature [34]. For all investigated composites PLA storage modulus hence mechanical properties downfall in between 60 and 70 °C.

### 3.5. Mechanical properties

Table 5 discloses the mechanical properties of investigated materials. As it is well known, composites can exhibit deteriorated mechanical properties with respect untreated polymer if a higher filler content is added to the formulation. A clear example was observed in PLA loaded with 50 phr ATH with respect to neat PLA. Tensile strength, strain at break and tenacity of PLA\_ATH<sub>50</sub> are

lower than those of neat PLA. On the other hand, PLA Young's modulus has been remarkably increased (+43%) due to the high ATH content (2413 vs. 1695 MPa for PLA\_ATH<sub>50</sub> and PLA, respectively).

Taking in account that the reference sample contains a flame retardant, mechanical properties of the composite materials using KFs and ATH were compared to those of PLA\_ATH<sub>50</sub> and PLA\_ATH<sub>30</sub>. According to the collected data (Table 5), PLA Young's modulus is not significantly affected when 10, 5 and 3 phr KFs are added as fillers to polymer matrix (1717, 1692, 1768 vs. 1695 MPa for PLA\_KF<sub>10</sub>, PLA\_KF<sub>5</sub>, PLA\_KF<sub>3</sub> and PLA, respectively).

PLA tensile strength is reduced when the highest KF content (10 phr) is used, from 56 to 28 MPa with respect to PLA\_ATH<sub>50</sub>. However, lower KF contents (5 and 3 phr) exhibit similar tensile strength values with respect to PLA\_ATH<sub>50</sub> (58 and 53 MPa for PLA\_KF<sub>5</sub> and PLA\_KF<sub>3</sub> samples, respectively). The strain at break and tenacity are significantly affected by KF content; indeed, when the highest KF content is used (10 phr), strain at break is reduced from 3.2 to 2.2% and tenacity passes from 0.9 to 0.3 MPa in comparison with PLA\_ATH<sub>50</sub>.

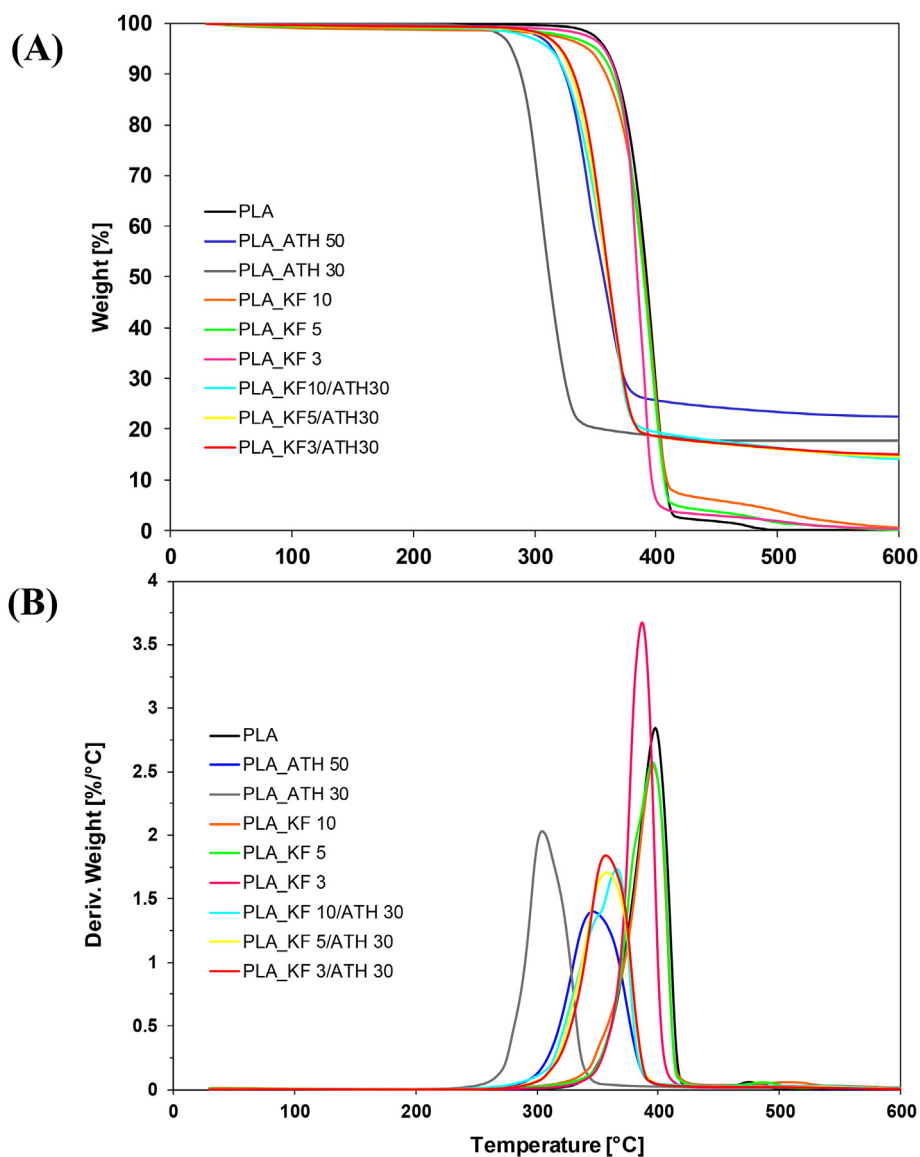


Fig. 6. TG (A) and dTG (B) curves of PLA and composites with KFs and ATH in air.

Table 3

TGA data of neat PLA and composites in nitrogen and air.

Sample	Nitrogen			Air		
	T <sub>10%</sub> [°C]	T <sub>max</sub> <sup>a</sup> [°C]	Residue at 600 °C [%]	T <sub>10%</sub> [°C]	T <sub>max</sub> <sup>a</sup> [°C]	Residue at 600 °C [%]
PLA	334	369	0.3	367	397	0.0
PLA_ATH <sub>50</sub>	290	316	23.3	325	344	22.5
PLA_ATH <sub>30</sub>	292	310	16.5	288	304	17.7
PLA_KF <sub>10</sub>	305	359	4.8	358	395	0.5
PLA_KF <sub>5</sub>	315	360	3.6	364	395	0.1
PLA_KF <sub>3</sub>	319	362	2.5	366	385	0.3
PLA_KF <sub>10</sub> /ATH <sub>30</sub>	285	310	19.3	325	365	14.2
PLA_KF <sub>5</sub> /ATH <sub>30</sub>	288	313	19.3	330	358	14.6
PLA_KF <sub>3</sub> /ATH <sub>30</sub>	285	319	16.8	332	355	15.0

<sup>a</sup> From derivative curves (Figs. 5B and 6B).

The opposite behaviour has been observed with lower KF contents (5 and 3 phr). Strain at break increases from 2.2 to 4.4 and 4.0% and tenacity passes from 0.9 to 1.2 and 1.1 MPa for PLA\_KF<sub>10</sub>, PLA\_KF<sub>5</sub> and PLA\_KF<sub>3</sub>, respectively.

Similar mechanical behaviour has been observed when KFs are


added in combination with ATH. Using the same ATH loading (30 phr) and 10 phr KFs (PLA\_KF<sub>10</sub>/ATH<sub>30</sub> in Table 5), PLA tensile strength, strain at break and tenacity are similar to sample with only 30 phr ATH. However, with low KF contents (PLA\_KF<sub>3</sub>/ATH<sub>30</sub> and PLA\_KF<sub>5</sub>/ATH<sub>30</sub> samples), tensile strength, strain at break and




**Table 4**  
Flammability data of neat PLA and composites following the UL94 classification (sample thickness = 3 mm).

Sample	UL94 classification
PLA	NC <sup>a</sup>
PLA_ATH <sub>50</sub>	V0
PLA_ATH <sub>30</sub>	V2
PLA_KF <sub>10</sub>	V2
PLA_KF <sub>5</sub>	V2
PLA_KF <sub>3</sub>	V2
PLA_KF <sub>10</sub> /ATH <sub>30</sub>	V0
PLA_KF <sub>5</sub> /ATH <sub>30</sub>	V0
PLA_KF <sub>3</sub> /ATH <sub>30</sub>	V0

<sup>a</sup> NC: Not classifiable.

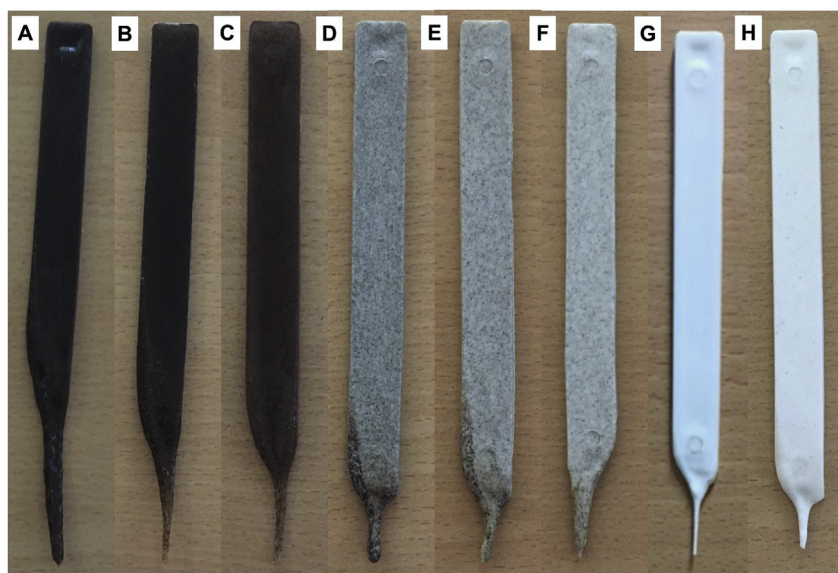

**Fig. 7.** Digital pictures of samples under investigation after UL94 tests: A) PLA\_KF<sub>10</sub>, B) PLA\_KF<sub>5</sub>, C) PLA\_KF<sub>3</sub>, D) PLA\_KF<sub>10</sub>/ATH<sub>30</sub>, E) PLA\_KF<sub>5</sub>/ATH<sub>30</sub>, F) PLA\_KF<sub>3</sub>/ATH<sub>30</sub>, G) PLA\_ATH<sub>30</sub> and H) PLA\_ATH<sub>50</sub>.

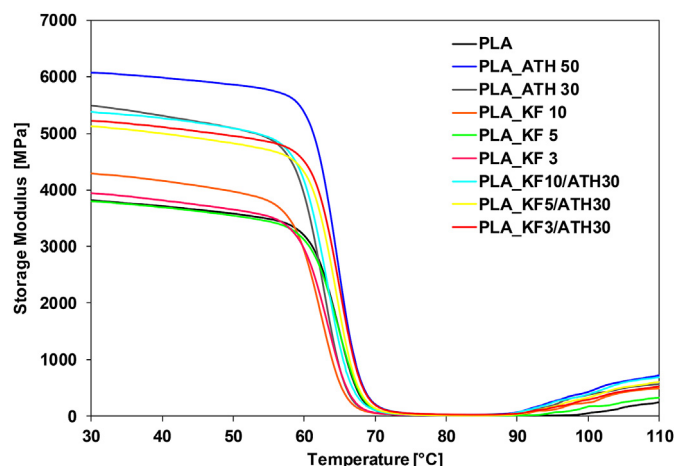

**Fig. 8.** Storage modulus ( $E'$ ) as a function of temperature for neat PLA and composites.

tenacity are higher than those of PLA\_ATH<sub>30</sub>. In this regard, KF restrict and slightly improve the mechanical properties depleted when adding ATH alone even at this low contents (PLA\_KF<sub>3</sub>/ATH<sub>30</sub> and PLA\_KF<sub>5</sub>/ATH<sub>30</sub> samples). However, the KFs alone are not so efficient to enhance PLA mechanical properties due to the low

concentrations used in this study. In general a significant improvement employing fibres as reinforcing agent has been reported for systems at high contents such as [35], recycled cellulose fibres in poly(lactic acid) composites [36], hemp fibres in polylactide [37] and kenaf fibres on Mater-Bi<sup>®</sup> composites [38].


According to the collected data, it is possible to conclude that high KF loadings with or without ATH produce a rigid and fragile material; conversely, low KF content allows for preparing less rigid materials. It is likely that somewhat fibre-polymer physical interactions favouring a better stress transfer [39] occur in these materials thanks to the KF/PLA good adhesion of KFs with polymer matrix, as already observed by SEM.

### 3.6. Rheological behaviour

Flow behaviour of neat PLA and composites was investigated under continuous simple and small amplitude oscillatory shear flows (SAOS). Fig. 9 depicts the shear viscosity as a function of shear rate of PLA and composites (Fig. 9A) and the complex viscosity versus frequency for small amplitude oscillatory shear tests (Fig. 9B). In Fig. 9A, neat PLA shows a mild shear-thinning behaviour at low shear rates (0.01–0.10 1/s). However, at higher shear rates (1.0–100 1/s), PLA exhibits a pronounced shear-thinning behaviour. All samples exhibit shear-thinning behaviour, which is consistent with reports for similar systems of fibre-reinforced

**Table 5**  
Mechanical properties of neat PLA and composites.

Sample	Young's modulus $\pm \sigma$ [MPa]	Tensile strength $\pm \sigma$ [MPa]	Strain at break $\pm \sigma$ [%]	Tenacity $\pm \sigma$ [MPa]
PLA	1695 $\pm$ 49	80 $\pm$ 4	6.2 $\pm$ 0.5	2.6 $\pm$ 0.4
PLA_ATH <sub>50</sub>	2431 $\pm$ 112	56 $\pm$ 6	3.2 $\pm$ 0.3	0.9 $\pm$ 0.2
PLA_ATH <sub>30</sub>	2464 $\pm$ 64	49 $\pm$ 8	2.7 $\pm$ 0.4	0.6 $\pm$ 0.2
PLA_KF <sub>10</sub>	1717 $\pm$ 133	28 $\pm$ 5	2.2 $\pm$ 0.3	0.3 $\pm$ 0.1
PLA_KF <sub>5</sub>	1692 $\pm$ 86	58 $\pm$ 2	4.4 $\pm$ 0.2	1.2 $\pm$ 0.1
PLA_KF <sub>3</sub>	1768 $\pm$ 149	53 $\pm$ 9	4.0 $\pm$ 0.5	1.1 $\pm$ 0.3
PLA_KF <sub>10</sub> /ATH <sub>30</sub>	2073 $\pm$ 102	43 $\pm$ 3	2.8 $\pm$ 0.3	0.6 $\pm$ 0.1
PLA_KF <sub>5</sub> /ATH <sub>30</sub>	1910 $\pm$ 158	63 $\pm$ 2	4.4 $\pm$ 0.1	1.4 $\pm$ 0.1
PLA_KF <sub>3</sub> /ATH <sub>30</sub>	1941 $\pm$ 113	65 $\pm$ 5	4.5 $\pm$ 0.4	1.5 $\pm$ 0.3

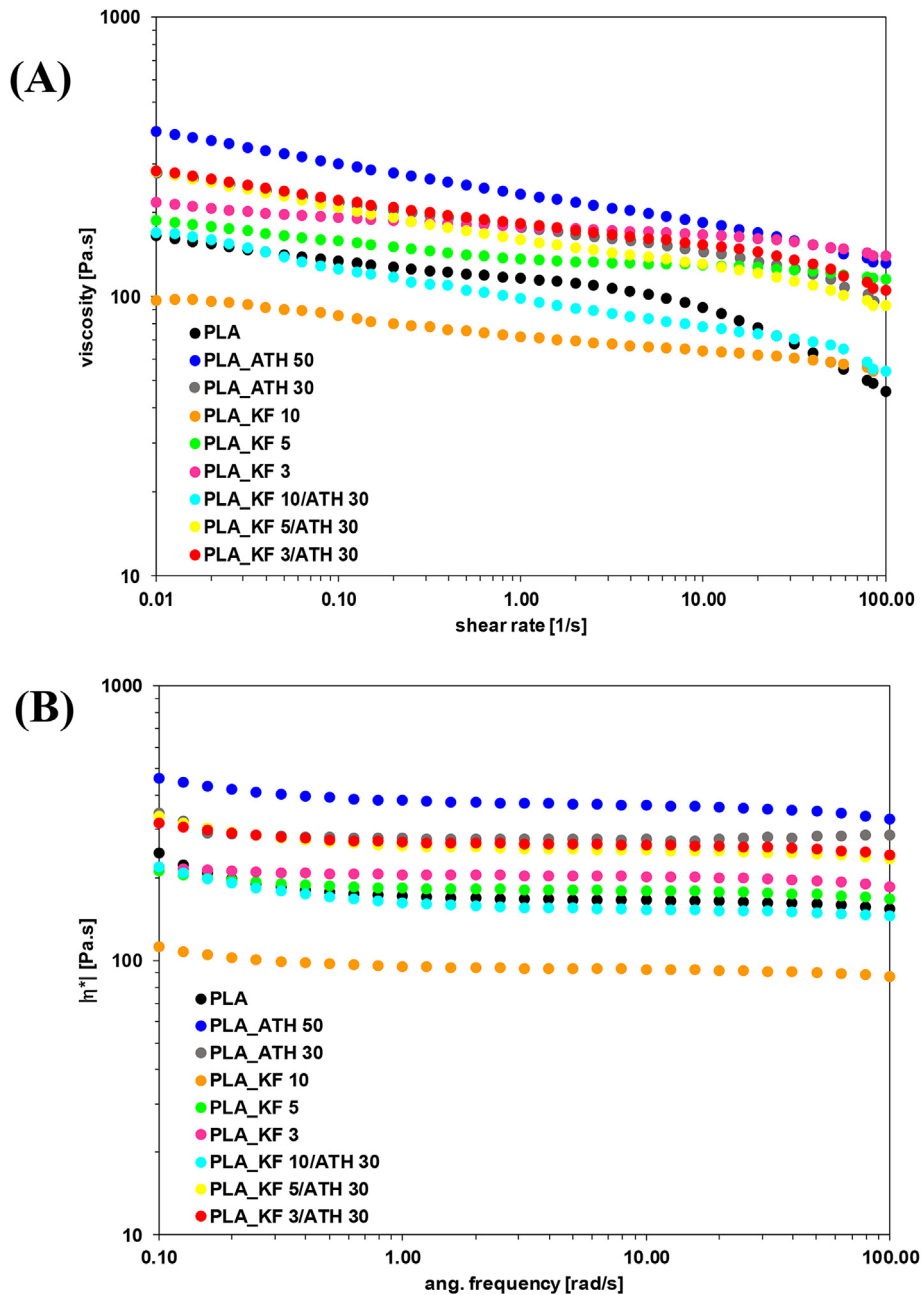

**Fig. 9.** A) Simple shear viscosity as a function of shear rate and B) Small amplitude oscillatory shear test showing the complex viscosity as a function of oscillatory frequency of neat PLA and composites.

polymer composites such as nylon in NR/SBR composites [40] and sisal in polypropylene [41]. PLA\_ATH<sub>50</sub> exhibits the highest shear viscosity of all samples at low shear rate ranges (0.01–0.10 1/s). At the same time, PLA\_ATH<sub>50</sub> shows a more pronounced shear-thinning behaviour in the second decade (0.10–1.0 1/s); on the contrary, in the last decade (10–100 1/s) a more pronounced shear-thinning behaviour is clearly observed. Samples containing ATH at 30 phr show a similar behaviour and their curves almost overlap (PLA\_ATH<sub>30</sub>, PLA\_KF<sub>3</sub>/ATH<sub>30</sub> and PLA\_KF<sub>5</sub>/ATH<sub>30</sub>), indicating that when ATH is added, KF at low contents does not significantly affects the rheology of the system except for the sample containing 5 phr of KFs which shows a viscosity reduction, evidencing that there is a minimum content of KFs to effectively reduce the viscosity of the systems when ATH is present in the polymer matrix. As far as KF-based composites are concerned, Fig. 9A shows that KF presence and content significantly affects PLA rheological behaviour. At low shear rate ranges (0.01–0.1 1/s), shear viscosity decreases by increasing KF content. Indeed, PLA\_KF<sub>10</sub> shows a lower shear viscosity than that of PLA\_KF<sub>5</sub> and the PLA\_KF<sub>3</sub> and the lowest value with respect to all the formulations under investigation. It is reasonable to guess that, at high KF content (higher fibre-polymer matrix contact), fibres are well oriented and contribute to better orientate PLA chains under flow testing [42]. It is important to highlight that, at high shear rate ranges, KF/PLA composites exhibit a mild shear thinning behaviour that is fundamental during transformation processes such as extrusion and injection moulding. In oscillatory flow (Fig. 9B), the complex viscosity does not show shear thinning behaviour but its reduction due to the KF content is analogous to that observed in simple shear flow (compare Fig. 9A and B).

On the other hand, all samples containing both KFs and ATH show a higher viscosity than their counterparts containing only KFs in both simple shear and oscillatory flow. However, KF at high content (PLA\_KF<sub>10</sub>/ATH<sub>30</sub>) shows similar diminishing effect on the viscosity for samples with 30 phr of ATH, as previously discussed, confirming that high KF content contributes in an important way to decrease the viscosity of the composites. On the basis of the collected rheological results, it is possible to conclude that KF


presence and content contribute to decrease the viscosity of the composites in a remarkable way, favouring and making easier their processability. This is likely due to the higher orientation of KFs near the shearing walls, causing a reduction in the bulk viscosity, as previously reported in some cases of other fibre-reinforced polymeric composites [42].

Fig. 10 reports the storage modulus ( $G'$ ) as a function of angular frequency under small amplitude oscillatory shear flow (SAOS) measurements of neat PLA and investigated composites. According to the plotted data in the 1.0–100 rad/s frequency range, most of the composites exhibit a  $G'$  modulus comparable with that of neat PLA, with the exception of PLA\_ATH<sub>50</sub> and PLA\_KF<sub>10</sub>/ATH<sub>30</sub>; indeed, PLA\_ATH<sub>50</sub> shows the highest modulus in the whole frequency and PLA\_KF<sub>10</sub>/ATH<sub>30</sub> exhibits the lowest one. However, in the 0.1–1.0 rad/s frequency range,  $G'$  value slightly depends on the composition of the investigated materials. Indeed, composites loaded with only KFs (regardless of their content) show a decrease of  $G'$  whereas the others containing both KFs and ATH exhibit an increase of  $G'$ , with respect to neat PLA. In addition, comparing the curve slopes at low frequency in Fig. 10 (values listed in Table 6), neat PLA, PLA\_ATH<sub>50</sub> and PLA\_KF<sub>3</sub>/ATH<sub>30</sub> show the lowest values that are almost equal, suggesting that these blends might behave as neat PLA during transformation process. The sample with the highest slope value is PLA\_KF<sub>3</sub>, this could be associated with poor particle-matrix interactions for this particular sample with low KF

**Table 6**

Slope values of curves reported in Fig. 10 in the low frequency range.

Sample	Slope in the 0.1 a 1.0 rad/s range
PLA	0.27
PLA_ATH <sub>50</sub>	0.26
PLA_ATH <sub>30</sub>	0.39
PLA_KF <sub>10</sub>	0.33
PLA_KF <sub>5</sub>	0.39
PLA_KF <sub>3</sub>	0.60
PLA_KF <sub>10</sub> /ATH <sub>30</sub>	0.57
PLA_KF <sub>5</sub> /ATH <sub>30</sub>	0.45
PLA_KF <sub>3</sub> /ATH <sub>30</sub>	0.28

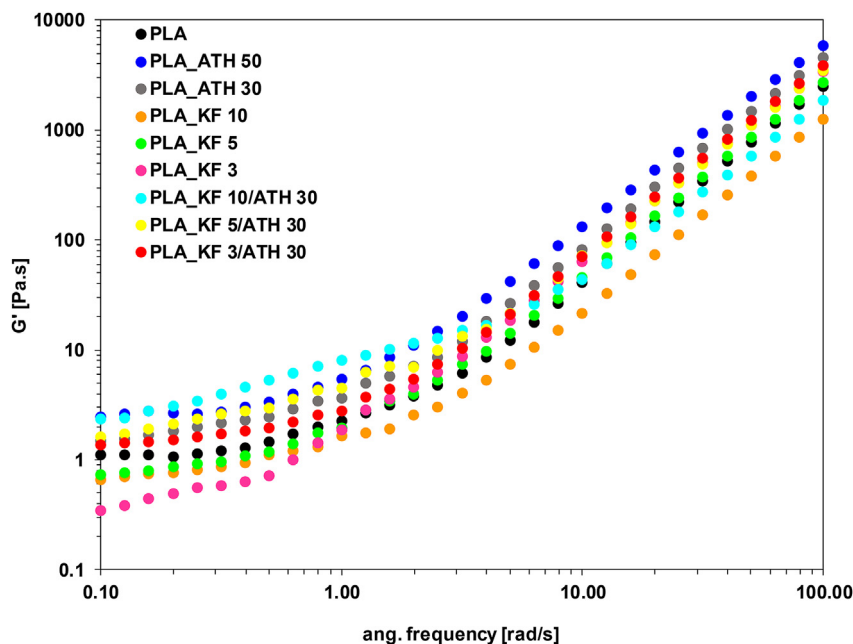

**Fig. 10.** Storage modulus ( $G'$ ) as a function of angular frequency in SAOS flow of neat PLA and composites.

content, which is consistent with the measured mechanical properties. Indeed, this sample did not improve tensile strength with respect to the high loaded ATH sample (PLA\_ATH<sub>50</sub>).

According to SAOS flow tests composites containing both KFs and ATH exhibit a higher elastic behaviour than those loaded with only KFs, as observed for the viscosity in both simple shear and oscillatory flow tests (see Fig. 9A and B).

#### 4. Conclusions

Poly(lactic acid) composites based on keratin fibres recovered from tannery industry wastes were prepared by melt-extrusion. The joint action with a traditional halogen-free flame retardant (namely, aluminium trihydroxide) was investigated. KFs have proven to be well embedded in polymer matrix as well as exhibit a good adhesion with PLA.

KFs have conferred remarkable flame retardant properties to PLA. Indeed, a low KF content (3 phr) has proven to be efficient for passing from NC (not classifiable) to V2 classification, according to the UL94 standard. Further improvements have been achieved exploiting the joint action between KFs (3 phr) and ATH (30 phr). With this formulation, PLA reached the V0 classification, the same categorization obtained for the target sample containing 50 phr ATH, but exhibiting higher mechanical properties i.e. tensile strength increased by 16%, strain at break by 40% and tenacity by 66% when ATH content was reduced from 50 phr to 30 phr + 3 phr KF content. Thus, replacing 20 phr ATH with 3 phr KFs has proven to be very advantageous from an economical and environmental point of view.

On the other hand, the formulations containing higher KF contents exhibited better flow properties, making easier the PLA processing.

The present work set the bases for a new application of the KFs derived from tannery industry wastes; indeed, it has been demonstrated that it is possible to easily prepare completely green polymeric composites with remarkable flame retardant and mechanical properties that might be exploited in electrical, electronic and automotive fields such as manufacturing flame retardant panels, cabinets or protective housing parts.

#### Funding

Part of this work was supported by CONCYTEG [090/2015 project].

#### Acknowledgments

The Authors would like to thank Mr. Leonardo Moreno, Dr. Omar Novelo and Mr. Victor Ramirez for rheological measurements, morphological observations and keratin fibre treatment.

#### Appendix A. Supplementary data

Supplementary data related to this article can be found at <http://dx.doi.org/10.1016/j.polydegradstab.2017.04.011>.

#### References

- [1] N. Reddy, Y. Yang, Biofibers from agricultural byproducts for industrial applications, *Trends Biotechnol.* 23 (1) (2005) 22–27.
- [2] E. Papadopoulou, D. Bikiaris, K. Chrysafis, M. Władyska-Przybylak, D. Wesolek, J. Mankowski, J. Kolodziej, P. Baraniecki, K. Bujnowicz, V. Gronberg, Value-added industrial products from bast fiber crops, *Ind. Crops Prod.* 68 (2015) 116–125.
- [3] J.J. Maya, T. Sabu, Biofibers and biocomposites, *Carbohydr. Polym.* 71 (2008) 343–364.
- [4] G. Koronis, A. Silva, M. Fontul, Green composites: a review of adequate materials for automotive application, *Compos Part B-Eng* 44 (2013) 120–127.
- [5] K.-Y. Lee, Y. Aitomäki, L.A. Berglund, K. Oksman, A. Bismarck, On the use of nanocellulose as reinforcement in polymer matrix composite, *Compos Sci. Technol.* 105 (2014) 15–27.
- [6] J. Müssig, M. Schmehl, H.-B. Von Buttlar, U. Schönfeld, K. Arndt, Exterior components based on renewable resources produced with SMC technology—considering a bus component as example, *Ind. Crops Prod.* 24 (2006) 132–145.
- [7] P.J. Herrera-Franco, L.T. Drzal, Comparison of methods for the measurement of fibre/matrix adhesion in composites, *Composites* 23 (1) (1992) 2–27.
- [8] O. Faruka, A.K. Bledzka, H.-P. Fink, M. Sain, Biocomposites reinforced with natural fibers: 2000–2010, *Prog. Polym. Sci.* 37 (2012) 1552–1596.
- [9] N. Saba, M. Jawaid, O.Y. Althman, M.T. Paridah, A review on dynamic mechanical properties of natural fibre reinforced polymer composites, *Constr. Build. Mater.* 106 (2016) 149–159.
- [10] J.R. Barone, W.F. Schmidt, C.F.E. Liebner, Compounding and molding of polyethylene composites reinforced with keratin feather fiber, *Compos Sci. Technol.* 65 (2005) 683–692.
- [11] M. Zhan, R.P. Wool, Mechanical properties of chicken feather fibers, *Polym. Compos* 32 (2011) 937–944.
- [12] B.O. Baba, U. Özmen, Preparation and mechanical characterization of chicken feather/PLA composites, *Polym. Compos* (2015) n/a.
- [13] G. Ramamurthy, B. Ramalingam, M.F. Katheem, T.P. Sastry, S. Inbasekaran, V. Thanveer, S.K. Das, A.B. Mandal, Total elimination of polluting chrome shavings, chrome, and dye exhaust liquors of tannery by a method using keratin hydrolysate, *ACS Sustain. Chem. Eng.* 3 (2015) 1348–1358.
- [14] V. Beghetto, V. Zancanaro, A. Scrivanti, U. Matteoli, G. Pozza, The leather industry: a chemistry insight Part I: an overview of the industrial process, *Sci. at ca' Foscari* (2013) 13–22.
- [15] Pollution Prevention Opportunities in the Tanning Sector Industry within the Mediterranean Region. Spain, ministry of the environment; autonomous government of catalonia: barcelona, file:///C:/Users/gsanchez/Downloads/cur\_eng%20(1).pdf, 2000, (Accessed 19 November 2016).
- [16] S. Bourbigot, G. Fontaine, Flame retardancy of polylactide: an overview, *Polym. Chem.* 1 (2010) 1413–1422.
- [17] ASTM D3590, Standard Test Methods for Total Kjeldahl Nitrogen in Water, American Society for Testing and Materials International, Philadelphia, 2011.
- [18] ASTM D3801, Standard Test Method for Measuring the Comparative Burning Characteristics of Solid Plastics in a Vertical Position, American Society for Testing and Materials International, Philadelphia, 2010.
- [19] ASTM D638, Standard Test Method for Tensile Properties of Plastics, American Society for Testing and Materials International, Philadelphia, 2014.
- [20] G. Wei, B. Bhushan, P.M. Torgerson, Nanomechanical characterization of human hair using nanoindentation and SEM, *Ultramicroscopy* 105 (2005) 248–266.
- [21] T. Harizi, S. Msahli, F. Sakli, M. Mekki, T. Khorchani, Surface morphology investigation of tunisian dromedary hair, *J. Agric. Sci. Technol.* A4 (2014) 454–459.
- [22] A. Thomas, D.P. Harland, S. Clerens, S. Deb-Choudhury, J.A. Vernon, G.L. Krsinic, R.J. Walls, C.D. Cornellison, J.E. Plowman, J.M. Dyer, Interspecies comparison of morphology, ultrastructure, and proteome of mammalian keratin fibers of similar diameter, *J. Agric. Food Chem.* 60 (2012) 2434–2446.
- [23] E. Zini, M. Scandola, Green composites: an overview, *Polym. Compos* 32 (2011) 1905–1915.
- [24] M. Zhan, R.P. Wool, Mechanical properties of chicken feather fibers, *Polym. Compos* 32 (2011) 937–944.
- [25] M. Brebu, I. Spiridon, Thermal degradation of keratin waste, *J. Anal. Appl. Pyrol* 91 (2011) 288–295.
- [26] F. Bosco, R.A. Carletto, J. Alongi, L. Marmo, A. Di Blasio, G. Malucelli, Thermal stability and flame resistance of cotton fabrics treated with whey proteins, *Carbohydr. Polym.* 94 (2013) 372–377.
- [27] J. Alongi, R.A. Carletto, F. Bosco, F. Carosio, A. Di Blasio, F. Cuttica, V. Antonucci, M. Giordano, G. Malucelli, Caseins and hydrophobins as novel green flame retardants for cotton fabrics, *Polym. Degrad. Stab.* 99 (2014) 111–117.
- [28] F. Carosio, A. Di Blasio, F. Cuttica, J. Alongi, G. Malucelli, Flame retardancy of polyester and polyester-cotton blends treated with caseins, *Ind. Eng. Chem. Res.* 53 (2014) 3917–3923.
- [29] J. Alongi, F. Cuttica, A. Di Blasio, F. Carosio, G. Malucelli, Intumescent features of nucleic acids and proteins, *Thermochim. Acta* 591 (2014) 31–39.
- [30] P. Hornsby, in: CA. Wilkie, A.B. Morgan (Eds.), *Fire Retardancy of Polymeric Materials*, Chap. 7: Fire-retardant Fillers, CRC Press, Boca Raton, 2010, pp. 163–166.
- [31] J. Alongi, A.R. Horrocks, in: J. Alongi, A.R. Horrocks, F. Carosio, G. Malucelli (Eds.), *Update on Flame Retardant Textiles: State of the Art, Environmental Issues and Innovative Solutions*, Chap. 2: Fundamental Aspects of Flame Retardancy, Smithers Rapra Technology Ltd, Shawbury, 2013, pp. 26–27.
- [32] K. Wrześniewska-Tosik, S. Zajchowski, A. Bryśkiewicz, J. Ryszkowska, Feathers as a flame-retardant in elastic polyurethane foam, *Fibres Text. East Eur.* 22 (2014), 1(103): 119–128.
- [33] E. Gallo, G. Sanchez-Olivares, B. Scharrel, Flame retardancy of starch-base biocomposites – aluminum hydroxide-coconut fiber synergy, *Polymer* 58 (5) (2013) 395–402.
- [34] X. Wang, C. Lu, C. Chen, Effect of chicken-feather protein-based flame retardant on flame retarding performance of cotton fabric, *J. Appl. Polym. Sci.* 131 (2014) 40584.

- [35] M. Jawaid, H.P.S.A. Khalil, A. Hassan, R. Dungani, A. Hadiyane, Effect of jute fibre loading on tensile and dynamic mechanical properties of oil palm epoxy composites, *Compos Part B-Eng* 45 (2013) 619–624.
- [36] M.S. Huda, A.K. Mohanty, L.T. Drzal, E. Schut, M. Misra, “Green” composites from recycled cellulose and poly(lactic acid): physico-mechanical and morphological properties evaluation, *J. Mater. Sci.* 40 (2005) 4221–4229.
- [37] M.A. Sawpan, K.L. Pickering, A. Fernyhough, Improvement of mechanical performance of industrial hemp fibre reinforced polylactide biocomposites, *Compos Part A* 42 (2011) 310–319.
- [38] G. Lo Re, M. Morreale, R. Scaffaro, F.P. La Mantia, Kenaf-filled biodegradable composites: rheological and mechanical behaviour, *Polym. Int.* 61 (2012) 1542–1548.
- [39] A.R. Kakroodi, Y. Kazemi, D. Rodrigue, Mechanical, rheological, morphological and water absorption properties of maleated polyethylene/hemp composites: effect of ground tire rubber addition, *Compos Part B-Eng* 51 (2013) 337–344.
- [40] S. Soltani, G. Naderi, M.H.R. Ghoreishy, Mechanical and rheological properties of short nylon fibre NR/SBR composites, *J. Rubb. Res.* 13 (2010) 110–124.
- [41] N. Le Moigne, M.V.D. Oever, T. Budtova, Dynamic and capillary shear rheology of natural fiber-reinforced composites, *Polym. Eng. Sci.* 53 (2013) 2582–2593.
- [42] M. Ho, H. Wang, J.-H. Lee, C. Ho, K. Lau, J. Leng, D. Hui, Critical factors on manufacturing processes of natural fibre composites, *Compos Part B-Eng* 43 (2012) 3549–3562.